

## Soy Ink Vehicles from Waste Frying Oils for Green Printing Technology

<sup>1</sup>Sivaphol Phunphoem, <sup>2</sup>Pitt Supaphol and <sup>1</sup>Onusa Saravari

<sup>1</sup>Department of Materials Science, Faculty of Science, Chulalongkorn University, Bangkok, Thailand

<sup>2</sup>The Petroleum and Petrochemical College, Chulalongkorn University, Bangkok, Thailand

---

**Abstract:** The objectives of this study were to synthesis printing ink vehicles via thermal polymerization from waste frying soybean oil. Properties of products with a variety of Waste frying oil (W) to Virgin oil (V) weight ratios (W:V ratios) were determined. We found that both viscosities and molecular weights of the obtained printing ink vehicles increased as the W:V ratios increased. Therefore, different types of eco-friendly printing inks for various printing applications can be produced. In addition, the cost and polymerization time of ink vehicle production could be reduced by using the waste frying oil.

**Key words:** Waste frying oil, soy ink vehicle, green printing technology, products, ratio

---

### INTRODUCTION

In recent years, much attention has been paid on the problem of waste frying oils from households and food industries. These oils usually contain a large number of harmful decomposition products occurring from hydrolysis, oxidation and polymerization (Cvengros and Cvengrosova, 2004; Kulkarni and Dalai, 2006; Choe and Min, 2007; Ng *et al.*, 2014). Normally, they are poured down to the drain or spilled onto ground which causes many environmental problems. Sometimes, they are integrated into the food chains through animal meat that bring potential negative effects on human health. Various approaches have been studied utilizing these residues in any way that is not harmful to human beings, for example, biodiesel production (Kulkarni and Dalai, 2006). Vegetable oil based-printing inks, the nonpetroleum-based printing inks produced from vegetable oils have received more attention since the petroleum crisis in 1970's. Due to the environmental benefits such as sustainable raw materials and few Volatile Organic Compounds (VOCs), vegetable oil based-printing inks play an essential role for green printing technology. Several studies have demonstrated the possibility of producing vegetable oil based-printing inks via thermal polymerization from various vegetable oils such as soybean, canola, cottonseed, safflower and sunflower oil (Erhan and Bagby, 1991, 1994, 1995; Erhan *et al.*, 1992). Results show that these printing inks had physical properties that met the industry standards for lithographic and letterpress newsprint applications

and soybean oil-based ink vehicles were proved to degrade faster than the commercial petroleum-based vehicles (Erhan, 1995). Recently, many manufacturers have made extensive efforts to develop products from soybean oil-based formulations. Therefore, soy inks are applied nowadays in many printing applications. For synthesis via thermal polymerization, the vegetable oil is heated at elevated temperature in which the unsaturated bonds of triglycerides are thermolytic to form radical species and undergo polymerization to form high molecular weight polymers (Erhan *et al.*, 1992). However, the crucial hindrance in the commercialization of vegetable oil based-printing ink is the greater price of virgin vegetable oils and also the high energy consumption during the manufacturing process.

Waste frying oils which are priced 2-3 times lower than virgin vegetable oils could be promising alter-native raw materials for the manufacture of printing inks. Additionally, the structural transformation of oil during frying is in a similar manner to that of vegetable oil based-ink vehicles produced via thermal polymerization (Cvengros and Cvengrosova, 2004; Choe and Min, 2007; Mehta and Swinburn, 2001; Zhang *et al.*, 2012). Thus, by using these waste frying oils, it is not only prevents serious environmental pollution but also provides the positively influences on the reduction of the final cost of printing inks. In this research we attempted to prepare eco-friendly printing ink vehicles from waste frying soybean oil blending with virgin oil at different weight ratios. The effect of waste frying oil composition on

properties of the soy ink vehicles was studied. The printing inks based on the obtained ink vehicles were also prepared to evaluate the potential use of the obtained vehicles.

## MATERIALS AND METHODS

Waste frying soybean oil was collected after being used several times for frying purposes at small shops within Chulalongkorn University, Thailand. Virgin soybean oil was purchased from Thai Vegetable Oil Public Company Limited, Thailand and used as received. Activated bleaching earth (Wonder Earth NK 309) was a gift from Bomnet Corporation Co., LTD., Thailand. Carbon black was purchased from Chemical Village Co., Ltd., Thailand.

**Synthesis of ink vehicles and printing inks:** Prior to synthesis, waste frying soybean oil was filtered to eliminate discernible impurities. The filtrated oil was then gently stirred for 2 h in the presence of 5% w/w of activated bleaching clay at 80°C under nitrogen atmosphere for decolorization. After that, the mixture was centrifuged and filtered to remove the as-absorbed clay. To synthesis the soy ink vehicles, the waste frying soybean oil was blended with virgin oil at various weight ratios and placed in a 2000 mL three-necked reaction flask equipped with a mechanical stirrer. The weight ratios of waste oil to virgin oil were varied from 0:100, 30:70, 50:50, 70:30 and 100:0. The blending oil was pre-treated with nitrogen gas for 10 min to eliminate oxygen gas in the mixture and then heated at 300°C for 4 h under nitrogen atmosphere. After which time, the obtained vehicle was allowed to cool to room temperature, degassed and kept in a vacuum bottle until further investigation. To evaluate the possible use of the obtained ink vehicle as printing ink binder, black printing inks were prepared by mixing the asprepared vehicles with carbon black (10 %w/w). The mixtures were vigorously stirred at 70°C for 12 h. The viscosity, ink tack and rub resistance of the obtained printing inks were also determined.

**Characterization and property measurements:** The physical properties of raw materials as well as the asprepared vehicles were examined with regard to Iodine Value (IV), Acid Value (AV), Molecular weight ( $M_w$ ), viscosity and color. The iodine value was determined with modified method based on ASTM D1959. The acid value was calculated based on ASTM D1980. The weight average molecular weight was determined by means of a GPC system (Shimadzu class-VP, Shimadzu Scientific Instruments, Columbia, MD, USA). The viscosities of

both prepared ink vehicles and printing inks were measured using a Brookfield DV-III programmable viscometer (Brookfield Engineering Labs, Stoughton, MA USA). The color was determined by comparison with the color of standard Gardner solutions. The chemical structures were characterized using a Nicolet FTIR spectrophotometer (Model Thermo Nicolet NEXUS 670; Nicolet Instrument Inc., Madison, WI, USA). Ink Tack was measured by Tack Tester (Model IGT Tack Tester 450; IGT Testing System Inc., USA) based on ASTM D4361. Ink rub resistance was measured by an Ink rub tester (Model Digital Ink rub Tester 10-18-01-0001; TMI Group of Companies, USA) based on ASTM D526

## RESULTS AND DISCUSSION

**Properties of waste frying soybean oil:** Table 1 illustrates the properties of waste frying oil in comparison with those of virgin oil. The iodine value which measures the degree of unsaturation of oil decreased from 123 for virgin oil to 91 g I<sub>2</sub> 100 g<sup>-1</sup> for waste frying oil. The waste frying oil had a molecular weight of 2,206 g mol<sup>-1</sup> which is higher than that of virgin oil (1,663 g mol<sup>-1</sup>). In addition, the oil was darker and its acid value increased after frying. In order to study the chemical transformation of waste frying oil, FTIR spectrum was analyzed. Figure 1 illustrates the FTIR spectrum of the waste frying oil in comparison with that of the virgin soybean oil. The characteristic absorption peaks of the virgin oil coincided with the general evidence of triglyceride structures, presenting absorption peaks at 3009 cm<sup>-1</sup> (C-H stretching), 2926 cm<sup>-1</sup> and 2855 cm<sup>-1</sup> (C-C-H stretching), 1746 cm<sup>-1</sup> (C=O stretching of esters) and 1650 cm<sup>-1</sup> (C=C stretching). For waste frying oil, its FTIR spectrum is identical with that of virgin soybean oil except the decrease in absorption

Table 1: Properties of virgin and waste frying soybean oils

| Types of oils | $M_w$<br>g mol <sup>-1</sup> | IV<br>(g I <sub>2</sub> 100 g <sup>-1</sup> ) | AV<br>(mg KOH g <sup>-1</sup> ) | Color<br>(Gardner) |
|---------------|------------------------------|---|---------------------------------|--------------------|
| Virgin oil    | 1.663                        | 123   | 0.22                            | 1.5                |
| Waste oil     | 2.206                        | 91  | 0.48                            | 4.0                |

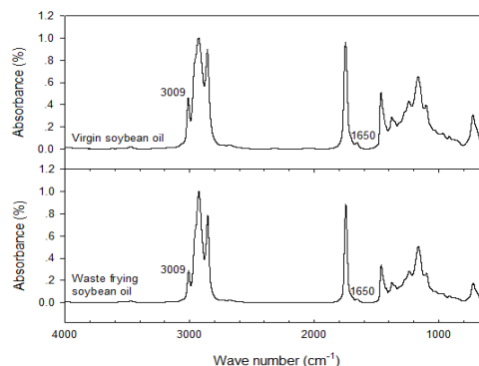


Fig. 1: FTIR spectra of waste oil and virgin soybean oil



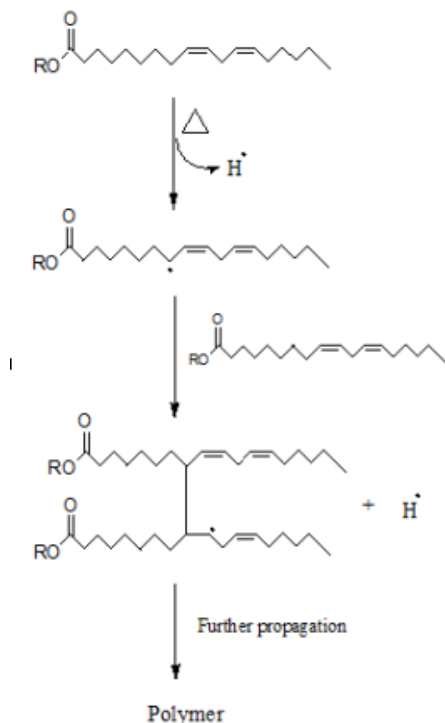


Fig. 3: Thermal polymerization mechanism of ink vehicles in inert atmosphere (Choe and Min, 2007)

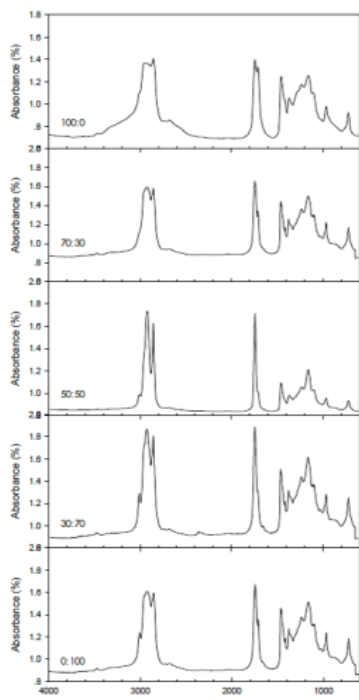


Fig. 4: FTIR spectra of the as-prepared printing ink vehicles with various Waste oil to Virgin oil (W:V) weight ratio

Table 3: The properties of black printing inks prepared from soy ink vehicles with various Waste frying oil to Virgin oil (W:V) weight ratio

| w:v ratio  | Ink viscosity (poise) | Ink tack (gm) | Rub resistance (%) |
|------------|-----------------------|---------------|--------------------|
| 0:10050:50 | 66.25                 | 1.571         | 82.3820            |
| 100:0      | 23.30                 | 3.37          | 54.0000            |

are presented in Table 3. The obtained printing inks are characterized by viscosities from 6-23.3 poises, tack values from 1.57-3.37 gm and rub resistance from 54- 82.3%. The typical viscosities of a black letterpress new ink and black lithographic news ink are in the range of about 5-12 and 13-24 poises, respectively while the tack values for letterpress inks are about 2.6-3.4 gm and about 3.5-4.8 gm for lithographic inks (Erhan *et al.*, 1992). The printing ink based on 100% waste frying oil (W:V = 100:0) had the highest tack value probably due to its highest viscosity (Izdebska and Thomas, 2015). Tack values of these inks were lower than the typical values. However, better tack value of the formulated inks can be achieved by adding appropriate additives. The data shown in Table 3 suggest that the 100% waste frying soybean oil-based ink is suitable for lithographic application, while the other two are suitable for making letterpress inks.

For rub resistance, the result was analyzed in term of the amount of transfer ink from the tested printed sample to white paper. As shown in Table 3, the obtained ink from 100% waste frying soybean oil had the lowest rub resistance. This may be due to its highest viscosity affecting in decreased absorption of ink into the printed sample surface. However, further investigation on printing ink formulations based on waste frying oil will be continued and we expect that waste soybean frying oil could be a promising alternative raw material for the manufacture of green printing inks.

### CONCLUSION

Waste frying soybean oil-based printing ink vehicles were successfully prepared via heat polymerization. A good relationship was found between the molecular weights and their viscosities of the as-prepared soy ink vehicles. With increasing content of waste frying oil, the polymerization was accelerated leading to the increase in molecular weight and viscosity of the synthesized vehicles. The obtained formulated inks are suitable for making lithographic and letterpress inks. This vehicle system can be easily modified to give products with a range of properties that suitable for making inks with a variety of printing applications. Results suggest that this approach can be used to produce environmental friendly and lower-cost ink vehicles from waste products such as used frying soybean oil.

#### **ACKNOWLEDGEMENTS**

Researchers would like to acknowledge the Department of Materials Science, Faculty of Science, Chulalongkorn University and the Petroleum and Petrochemical College, Chulalongkorn University for instrument support.

#### **REFERENCES**

- Choe, E. and D.B. Min, 2007. Chemistry of deep-fat frying oils. *J. Food Sci.*, 72: R77-R86.
- Cvengros, J. and Z. Cvengrosova, 2004. Used frying oils and fats and their utilization in the production of methyl esters of higher fatty acids. *Biomass Bioenergy*, 27: 173-181.
- Erhan, S.Z. and M.O. Bagby, 1991. Lithographic and letterpress ink vehicles from vegetable oils. *J. Am. Oil Chem. Soc.*, 68: 635-638.
- Erhan, S.Z. and M.O. Bagby, 1994. Polymerization of vegetable oils and their uses in printing inks. *J. Am. Oil Chem. Soc.*, 71: 1223-1226.
- Erhan, S.Z. and M.O. Bagby, 1995. Vegetable-oil-based printing ink formulation and degradation. *Ind. Crops Prod.*, 3: 237-246.
- Erhan, S.Z., M.O. Bagby and H.W. Cunningham, 1992. Vegetable oil-based printing inks. *J. Am. Oil Chem. Soc.*, 69: 251-256.
- Izdebska, J. and S. Thomas, 2015. *Printing on Polymers: Fundamentals and Applications*. 1st Edn., Elsevier Science, Amsterdam, Netherlands, ISBN:0323375006, Pages: 444.
- Kulkarni, M.G. and A.K. Dalai, 2006. Waste cooking oil an economical source for biodiesel: A review. *Ind. Eng. Chem. Res.*, 45: 2901-2913.
- Mehta, U. and B. Swinburn, 2001. A review of factors affecting fat absorption in hot chips. *Crit. Rev. Food Sci. Nutr.*, 41: 133-154.
- Ng, C.Y., X.F. Leong, N. Masbah, S.K. Adam, Y. Kamisah and K. Jaarin, 2014. Heated vegetable oils and cardiovascular disease risk factors. *Vascular Pharmacol.*, 61: 1-9.
- Robert, T., 2015. Green ink in all colors-printing ink from renewable resources. *Prog. Org. Coat.*, 78: 287-292.
- Zhang, Q., A.S.M. Saleh, J. Chen and Q. Shen, 2012. Chemical alterations taken place during deep-fat frying based on certain reaction products: A review. *Chem. Phys. Lipids*, 165: 662-681.