

Structural Behavior of Hybrid Reinforce Concrete Columns

Ammar Yasir Ali and Ammar Fawzi Latief

Department of Civil Engineering, University of Babylon, Babylon, Iraq

Abstract: This study presents experimental investigation of the structural behavior of reinforced concrete columns with hybrid cross-section (HSC and SFRC) and hybrid longitudinal reinforcement (steel and CFRP) bars. The experimental program included testing seventeen column specimens. One of column specimens was selected as a pilot column and sixteen columns were subdivided into 5 groups to study the effects of: type of concrete in the outer shell (HSC and SFRC), type of interface between core and shell (monolithic, surface intentionally roughened and surface intentionally roughened with shear connectors), type of main reinforcement and percentage of hybridization (ordinary steel and CFRP bars) and eccentricity to depth ratio (e/h) on the overall behavior, ultimate strength, deflection, cracking pattern, cracking load, modes of failure and ductility. All the column specimens have the same dimensions and tested under eccentric axial load only. The experimental work results showed that a significant improvement in the behavior and carrying capacity of the tested columns.

Key words: Hybrid column, monolithic, construction joint, shear connectors, HSC, SFRC

INTRODUCTION

Column-member, usually vertical or predominantly vertical, used primarily to support axial compressive load but that can also resist moment, shear or torsion. Columns have been used as part of the lateral-force-resisting system to resist combined axial load, moment and shear. From geometric view, the column is a member with a ratio of height-to-least lateral dimension exceeded (3), used primarily to support axial compressive load (Al-Haddad, 2016).

The outer concrete shell in a reinforced concrete column has a significant contribution in carrying the design loads. Such contribution may reach up to 40% of the ultimate loads, especially in a column having a small cross sectional area ($>900 \text{ cm}^2$). On the other hand, the outer shell acts to protect the steel reinforcement against corrosion and fire attack. Therefore, any damage or cracks in the outer shell will affect seriously both the strength and performance of the column (Al-Yassiri, 2017).

“Hybrid strength concrete refers to a new concept of casting two or more different types of concrete in the same section. Experimental and numerical studies for the behavior of reinforced hybrid concrete construction are summarized. Aziz, 2006 introduced experimental and theoretical investigations to study the shear behavior of hybrid reinforced concrete I-beams cast monolithically. A new manner by replacing (or strengthening) a certain part (s) or layer (s) of I-shaped reinforced concrete beams by

Steel Fiber Reinforced Concrete (SFRC) or High Strength Concrete (HSC) has been introduced (Anonymous, 2014). Malik, 2015 presented an experimental and theoretical investigations studied the effects of hybridization of T-shaped beam by HSC and SFRC, the presence of construction joint, using epoxy resin layer and shear connectors for flexural and shear behavior of simply supported reinforced concrete T-shaped beams. The results obtained from his adopted technique showed significant effects of SFRC and HSC on overall shear and flexural behavior of such beams. Mahdi, 2015 studied an experimental and theoretical investigations of the behavior and ultimate strength of double-symmetrical concrete corbels with hybrid reinforcement (steel and CFRP) bars subjected to vertical distributed applied load. He concluded that a significant improvement could occur in the behavior and carrying capacity in corbels of hybrid reinforcement in main tension or in horizontal reinforcement (stirrups) (Aziz, 2006). Al-Haddad, 2016 investigated experimental and theoretical investigations for shear and flexural behavior of reinforced concrete corbel-column systems made of hybrid concrete at the corbel-column connection region. The results that obtained from the experimental study was found that changing corbel concrete type from NSC-SFRC or HSC in shear and flexural behavior were increased the strength capacity and the cracking loads compared with homogenous NSC systems having same (a/d) ratio (Mahdi, 2015). Al-Yassiri (2017) studied an experimental

and numerical investigation of structural behavior of one-way and two-way hollow core slabs made from Normal Strength Concrete (NSC) or Hybrid Strength Concrete (HYSC) and reinforced with different types of rebars, steel and CFRP reinforcing bars. The test results showed that the increase of the voids in the cross section of the slab to a certain limit leads to the weakening of the shearing resistance, reduce the ultimate load capacity and ductility of the slab compared with the solid slab (Malik, 2015).

Information about the response of the structural behavior of a concrete column with a cross section of hybrid concrete and hybrid reinforcement of steel and CFRP bars was not available. Furthermore, the presence of vertical construction joint in RC. Corbels with homogenous or hybrid concrete was not considered in previous studies”.

Experimental program

Details of specimen geometry and reinforcement: All columns are identical in shape and external dimensions. The model dimensions selected in the present study were a square section of 150×150 mm and a total length of 1300 mm. The length between brackets (middle portion) is 700 mm and the dimensions of the bracket are 150*250*300 mm. All columns are reinforced with eight (φ 8 mm) deformed steel bars as longitudinal reinforcement (p = 0.0178) [except (C₇) and (C₈)]. Columns (C₇ and C₈) are reinforced with four (φ 8 mm) deformed steel bars and eight (φ 6 mm) CFRP bars as longitudinal

reinforcement and concrete cover (20 mm). All columns are reinforced with ties (φ 4.5 mm@125 mm spacing) deformed steel bars. All columns are designed according to Anonymous (2014), Al-Haddad (2016) specifications. The dimensions and reinforcement details of test specimens are shown in Fig. 1.

Description of test groups: The experimental program comprises of five groups of column specimens with homogenous and hybrid cross-sections and hybrid longitudinal reinforcement. The first group consists of four columns (C₃-C₆). The main variables were types of concrete of the shell (H₂ or SFRC), the eccentricity of the axial load (E₁ or E₂) and monolithic casting between the concrete of the core and the concrete of the shell. The second group consists of two columns (C₇, C₈). The main variables were the type of the concrete of the shell (SFRC), the eccentricity of the axial load (E₁ or E₂), monolithic casting between the concrete of the core and the concrete of the shell and 50% hybridization of the longitudinal reinforcement (steel and CFRP bars). The third group consists of four columns (C₁₀-C₁₃). The main variables were types of concrete of the shell (H₂ or SFRC), the eccentricity of the axial load (E₁ or E₂) and presence of construction joint between the concrete of the core and the concrete of the shell with type of interface (surface intentionally roughened). The fourth group consists of four columns (C₁₄-C₁₇). The main variables were the same of the group three in addition to presence of shear connectors welded on the ties. Designations and details

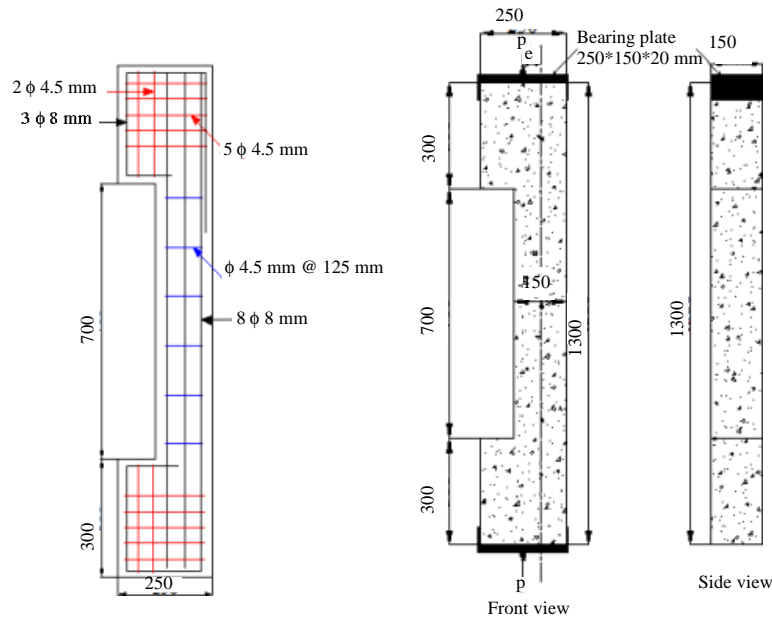


Fig. 1: Dimensions and reinforcement details of test specimens

of tested columns cross-sections are reported and presented in Fig. 2 as follows: symbols used in specimens designation refer to: C₁-C₁₇ sequence of specimens in the test groups, H₁: High strength concrete type 1, H₂: High strength concrete type 2, S: Steel fiber reinforced concrete (J): construction joint between core

and shell, (J_φ): construction joint between core and shell with shear connectors, (E₁), the amount of the load eccentricity 50 mm (e/h = 1/3), (E₂), the amount of the load eccentricity 75 mm (e/h = 1/2) and (R₅₀): replacement 50% of reinforcing steel bars with CFRP bars.

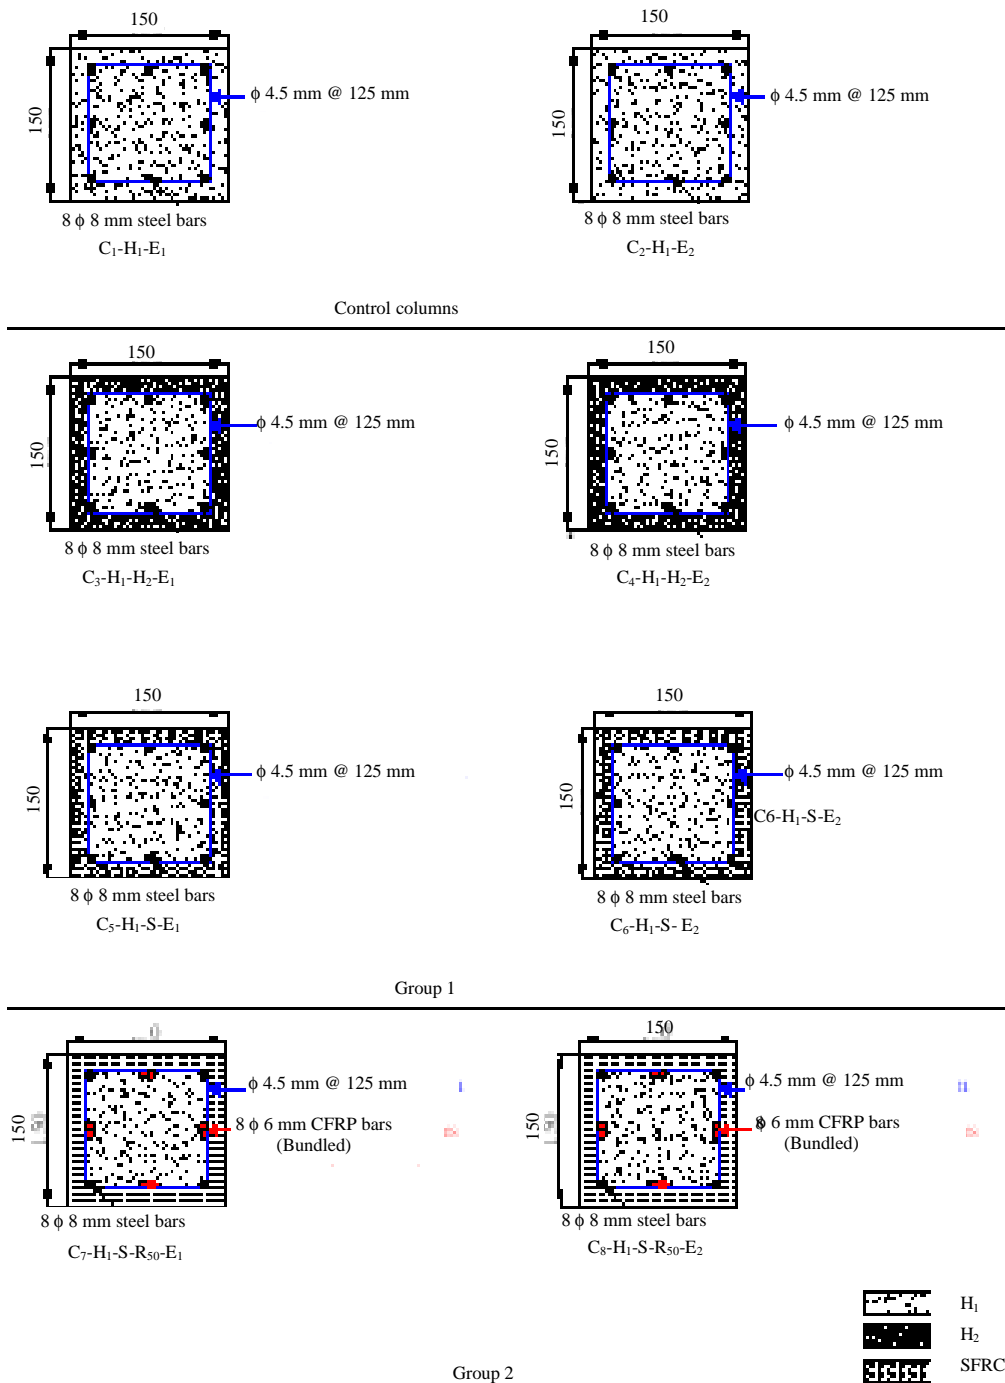


Fig. 2: Continue

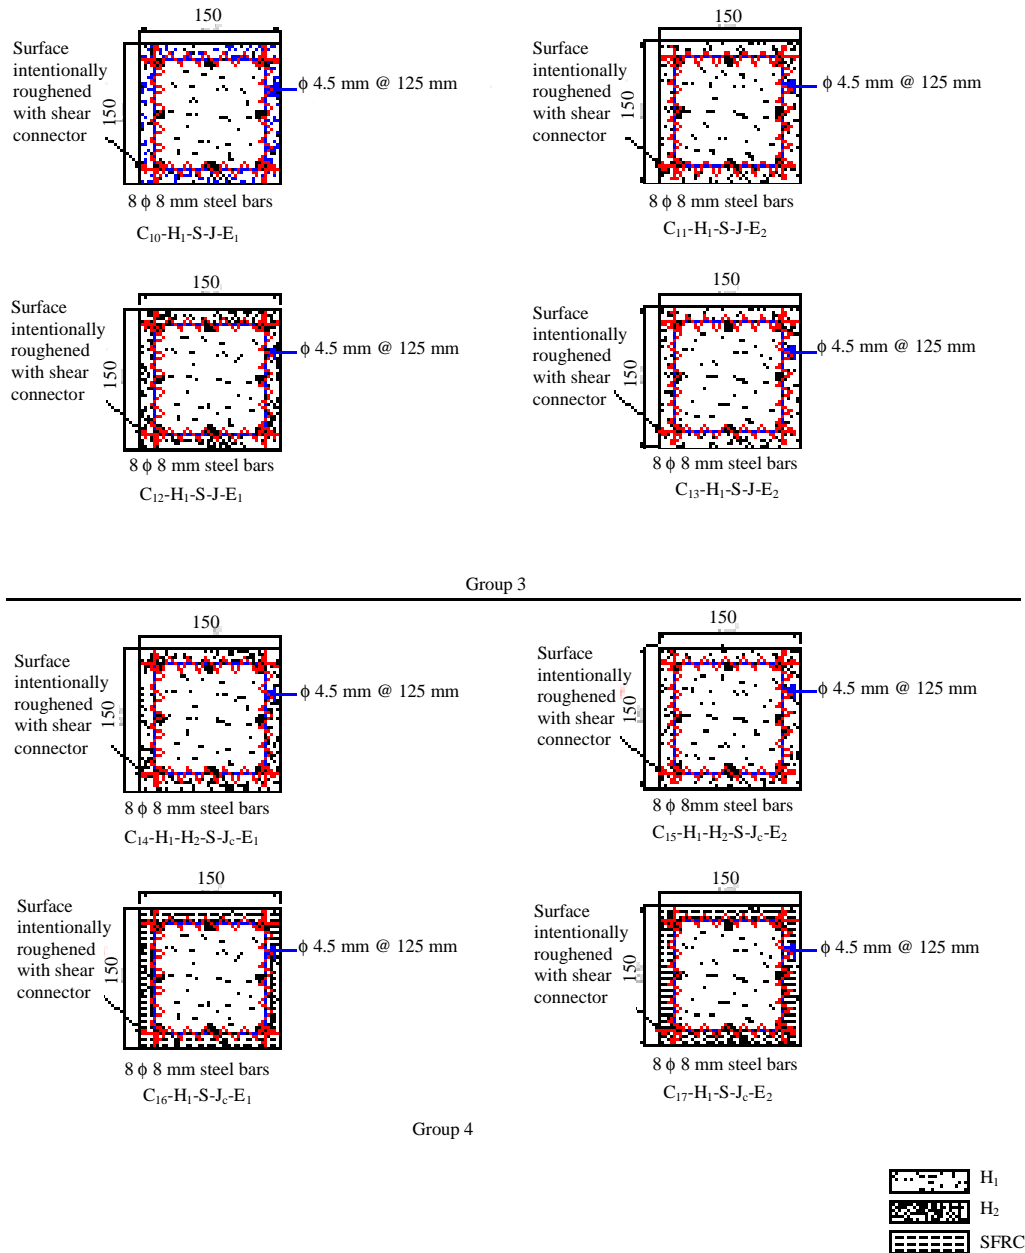


Fig. 2: Designation of test groups

MATERIALS AND METHODS

In the experimental program, tensile test of steel reinforcing bars was carried out on (φ 5 mm and φ 8 mm) deformed steel reinforcing bars with average yield strengths (f_y) of 602 and 517 MPa and average ultimate strengths of 602 and 586 MPa, respectively which conform to the American specification (ASTM-A370) (Anonymous, 1983). Also, CFRP bars of Aslan 201 series were used as longitudinal reinforcement of diameter 6mm and tensile strength of 2241 MPa with modulus of elasticity 124 GPa.

Three types of self compact concrete mixes (H₁, H₂, and SFRC) were used after several trial mixes for making the specimens. Mix proportions of H₁, H₂ and SFRC are illustrated in Table 1. The concrete was prepared with Portland cement (type 1), rounded, well graded gravel of 14 mm maximum size, Natural locally available fine aggregate of nominal maximum size 4.75 mm, fresh drinking water, Hyperplast PC200 high performance super plasticizing admixture and limestone powder as filler. Also, micro straight steel fibers (0.2×13 mm) with Volume fraction ($V_f = 1.0\%$) and aspect ratio ($L_f/D_f = 65$) were used in steel fiber reinforced concrete.

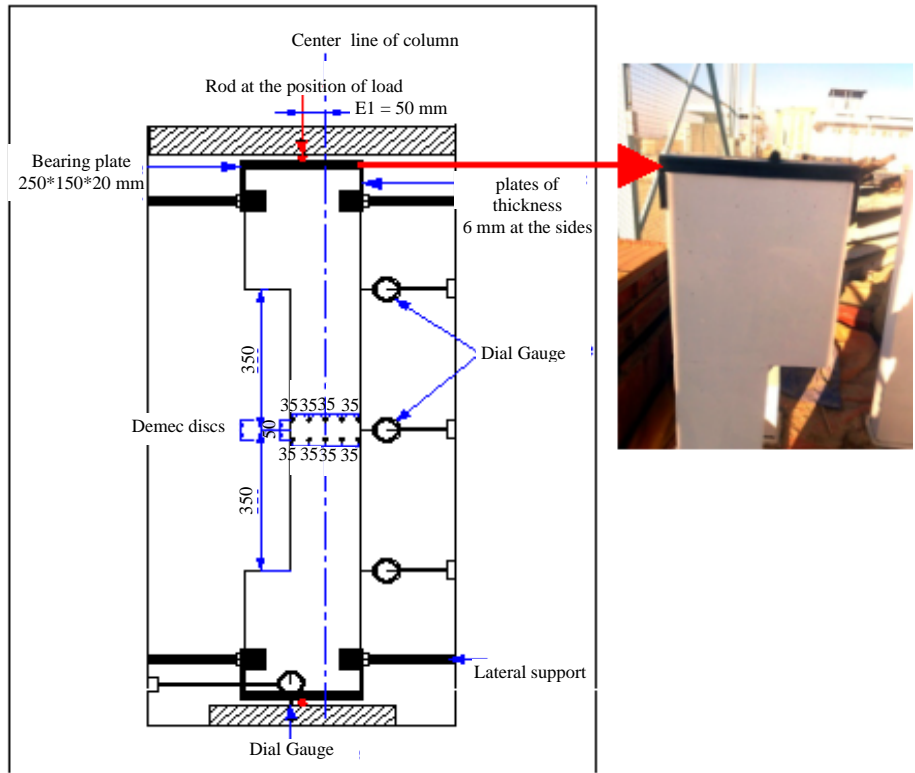


Fig. 3: Loading system

Table 1: Selected trial mixes for fresh and hardened SCC

Materials	Quantity (km ³)		
	H ₁	H ₂	SFRC
Cement	400	500	400
Gravel	800	840	800
Sand	850	871	850
Water	210	170	210
Hyperplast PC 200	7.20	12	7.20
Filler	120	100	120
SF	78

Testing: Hydraulic universal testing machine was used to test the column specimens as well as the control specimens. The testing machine has a capacity of (2000 kN). All the columns were supported axially and laterally unrestrained columns and tested up to failure. Two bearing plates of dimensions (250×150×20) mm with plates of the thickness 6 mm at the sides were used as caps for columns to prevent local failure. Also, lateral supports were provided to keep the column vertical before and after the loading. During each load step the corresponding lateral deflection and axial deformation were recorded as well as the first crack load. Dial gauges of accuracy 0.01mm were used to measure the lateral deflection and the axial deformation. The loading system is shown in Fig. 3. The compressive strength test of

concrete cylinders (150×300) mm and cubes (150×150×150) mm were carried out on H₁, H₂ and SFRC in accordance with BS1881-116 (Richart and Brown, 1934) at test time of each specimen with average values (51.34, 72.76, 55) MPa and (62.35, 88.30, 66.62) MPa for each type of concrete mix, respectively.

RESULTS AND DISCUSSION

The main aim of the present research is to study the effect of concrete hybridization technique on the structural behavior and ultimate strength of hybrid reinforced concrete column cast monolithically or with construction joint between the concrete of the core and the shell. The overall structural behavior of column specimens with hybrid cross-sections and hybrid reinforcement were investigated and discussed.

Control columns

Specimen C₁-H₁-E₁: Figure 4a shows the load deflection response of the column specimen C₁. The maximum applied load was 507 kN. The first crack in column appeared at 136 kN. The crack pattern of the specimen is shown in Fig. 4b.

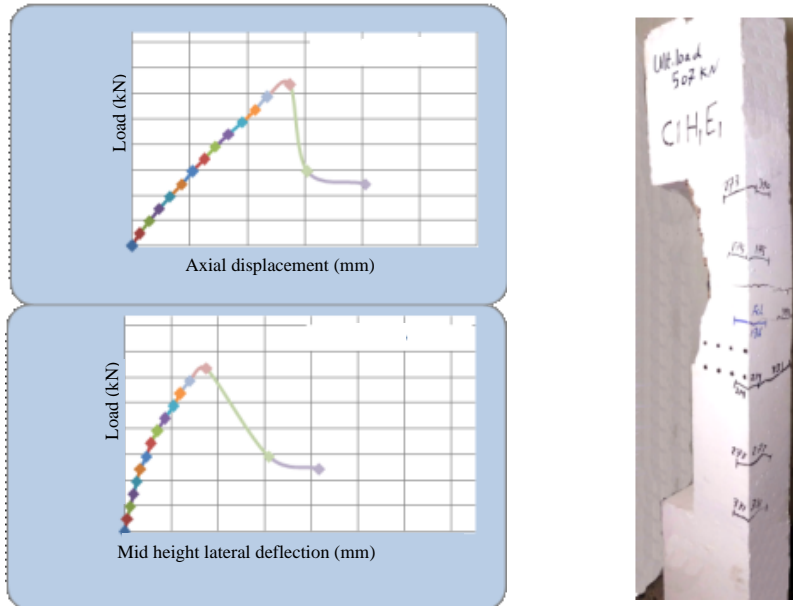


Fig. 4: a) Load-deflection of specimen C_1 and b) Crack pattern of C_1

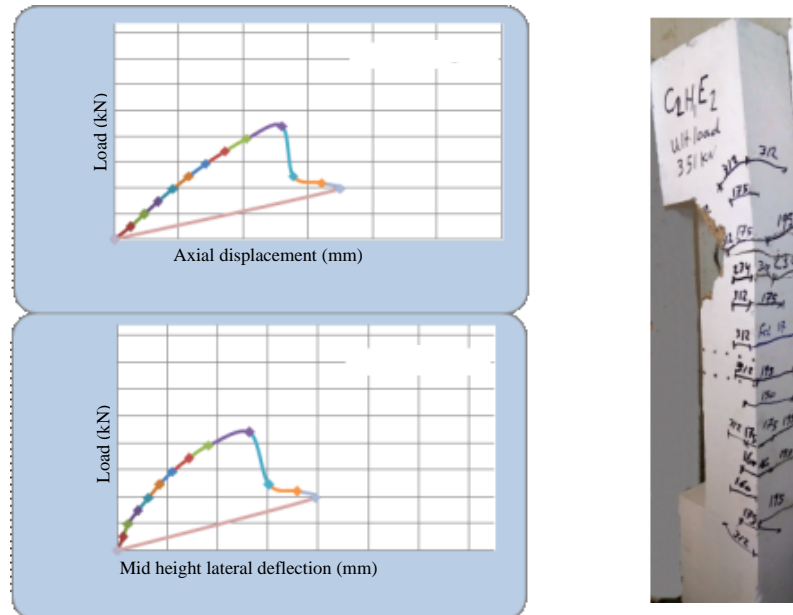


Fig. 5: a) Load-deflection of specimen C_2 and b) Crack pattern of C_2

Specimen C_2 - H_1 - E_2 : Figure 5a shows the load deflection response of the column specimen C_2 . The maximum applied load was 351 kN. The first crack in column appeared at 117 kN. The crack pattern of the specimen is shown in Fig. 5b.

Columns with monolithic casting

Columns of hybrid concrete cross section

Specimens C_3 - H_1 - H_2 - E_1 and C_4 - H_1 - H_2 - E_2 : In these

specimens, the outer shell of the columns were made with type H_1 . The first crack in columns appeared at concrete load (195 and 136 kN), respectively. The failure happened on the compression side suddenly at load (526 and 425 kN), respectively. Compared with control specimens (C_1 and C_2) there is an increase in the cracking load about (43.38 and 16.32%), respectively, also, there is an increase in the ultimate load capacity about (3.74 and 21.08%) and the ductility was decreased (1.13 and 5.68%), respectively.

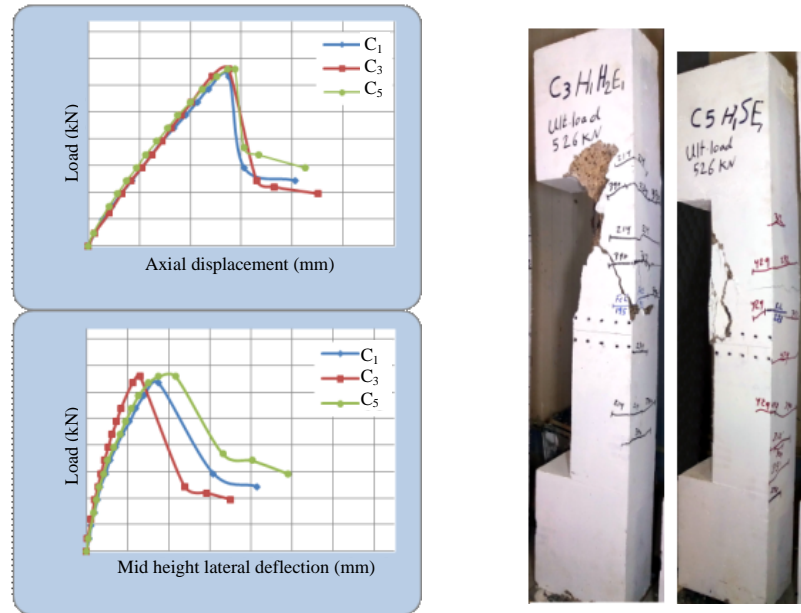


Fig. 6: a) Load-deflection of specimen C₃ and C₅ and b) Crack pattern of C₃ and C₅

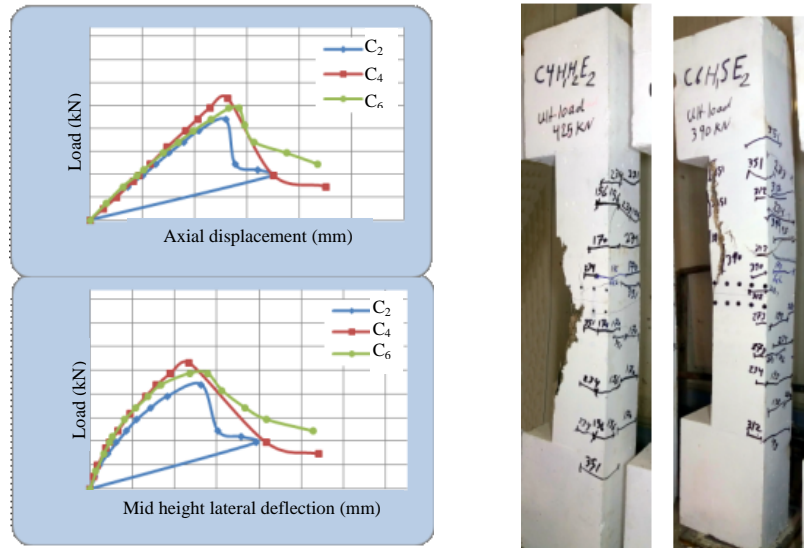


Fig. 7: a) Load-deflection of specimen C₄ and C₆ and b) Crack pattern of C₄ and C₆

Figure 6a and 7a show the load deflection response of the column specimens C₃ and C₄, respectively. Figure 6b and 7b show the crack pattern of the specimens C₃ and C₄, respectively.

Specimens C₅-H₁-S-E₁ and C₆-H₁-S-E₂: In these specimens, the outer shell of the columns were made with concrete type SFRC. The first crack in columns appeared load (273 and 175 kN), respectively. The failure at happened on the compression side gradually at

load (526 and 390 kN), respectively. Compared with control specimens (C₁ and C₂) there is an increase in the cracking load about (100 and 50%), respectively also, there is an increase in the ultimate load capacity about (3.74 and 11.11%) and the ductility was increased (8.74 and 4.54%), respectively. Figure 6a and 7a shows the load deflection response of the column specimens C₅ and C₆, respectively. Figure 6b and 7b shows the crack pattern of the specimens C₅ and C₆, respectively.

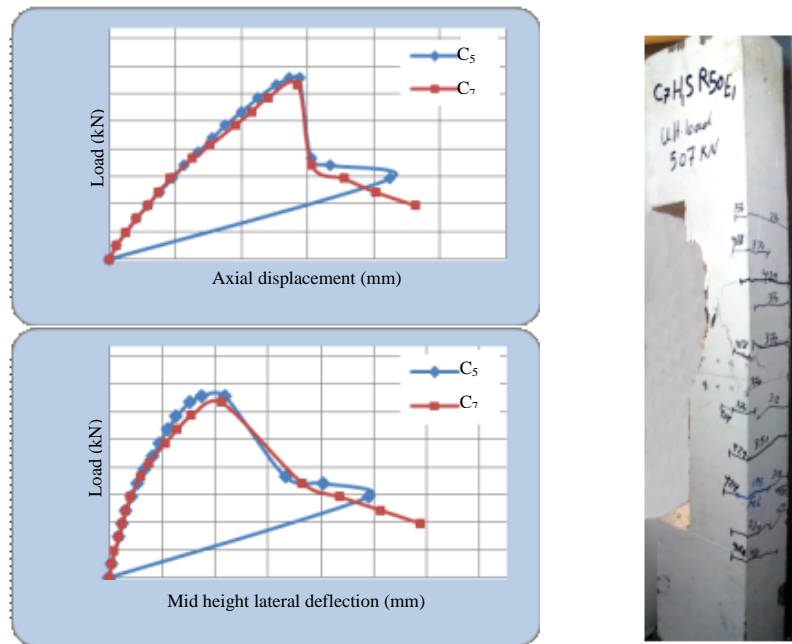


Fig. 8: a) Load-deflection of specimen C₇ and b) Crack pattern of C₇

Column specimens of hybrid reinforcement

Specimens C₇-H₁-S-R₅₀-E₁ and C₈-H₁-S-R₅₀-E₂ : In these specimens, the outer shell of the columns were made with concrete type SFRC and the longitudinal reinforcement hybridized with 50% CFRP bars .The first crack in columns appeared at load (195 and 117 kN), respectively. The failure happened on the compression side gradually at load (507 and 390 kN), respectively. Compared with reference specimens (C₅ and C₆) there is a decrease in the cracking load about (40 and 49.57%), respectively, also, there is a decrease in the ultimate load capacity about (3.75 and 0%) and the ductility was increased (1.04 and 5.43%), respectively. Figure 8a and 9a shows the load deflection response of the column specimens C₇ and C₈, respectively. Figure 8b and 9b shows the crack pattern of the specimens C₇ and C₈, respectively.

Column specimens with construction joints

Specimens C₁₀-H₁-H₂-E₁ and C₁₁-H₁-H₂-E₂ : In these specimens, the outer shell of the columns were made with concrete type H₁ and presence of construction joint between the core and the shell with interface type (surface intentionally roughened). The first crack in columns appeared at load (292 and 156 kN), respectively. The spalling happened on the compression side suddenly at load (604 and 487kN), respectively. Compared with reference specimens (C₃ and C₄) there is an increase in the cracking load about (49.74 and 14.70%), respectively also, there is an increase in the ultimate load capacity

about (14.82 and 14.59%) and the ductility was decreased (1.14 and 1.80%), respectively. Figure 10a and 11a shows the load deflection response of the column specimens C₁₀ and C₁₁, respectively. Figure 10b and 11b shows the crack pattern of the specimens C₁₀ and C₁₁, respectively.

Specimens C₁₂-H₁-S-J-E₁ and C₁₃-H₁-S-J-E₂ : In these specimens, the outer shell of the columns were made with concrete type SFRC and presence of construction joint between the core and the shell with interface type (surface intentionally roughened). The first crack in columns appeared at load (312 and 195 kN), respectively. The spalling happened on the compression side gradually at load (565 and 409 kN), respectively. Compared with reference specimens (C₅ and C₆) there is an increase in the cracking load about (129.41 and 66.66%), respectively also, there is an increase in the ultimate load capacity about (11.44 and 16.52%) and the ductility was decreased (6.25-2.17%), respectively. Figure 10a and 11a show the load deflection response of the column specimens C₁₂ and C₁₃, respectively. Figure 10b and 11b show the crack pattern of the specimens C₁₂ and C₁₃, respectively.

Specimens C₁₄-H₁-H₂-J_c-E₁ and C₁₅-H₁-H₂-J_c-E₂ : These specimen are the same of the specimens C₁₀ and C₁₁ with presence of shear connectors across the construction joint. The first crack in columns appeared at load (156 and 136 kN), respectively. The spalling happened on the side suddenly at load compression (624 and

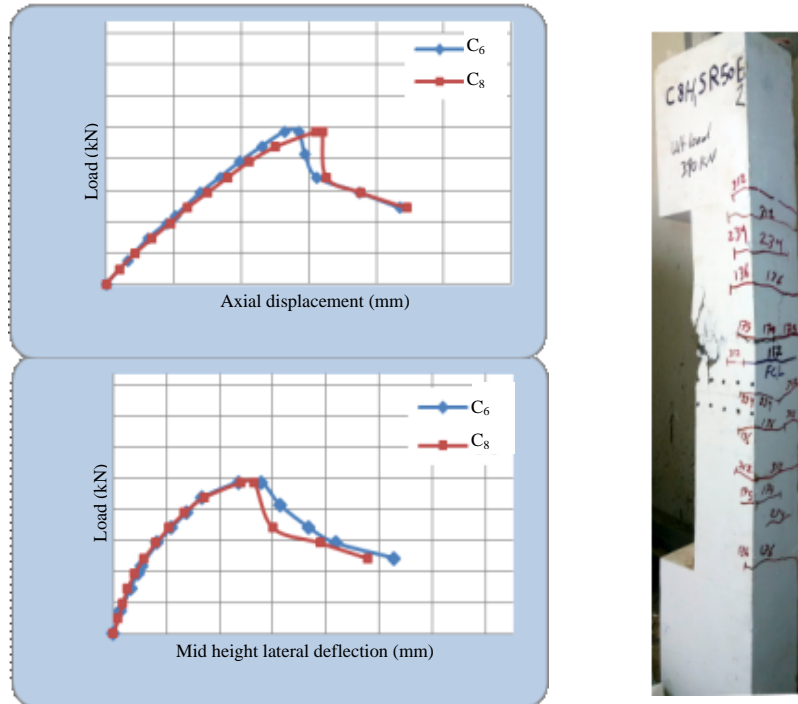


Fig. 9: a) Load-deflection of specimen C₈ and b) Crack pattern of C₈

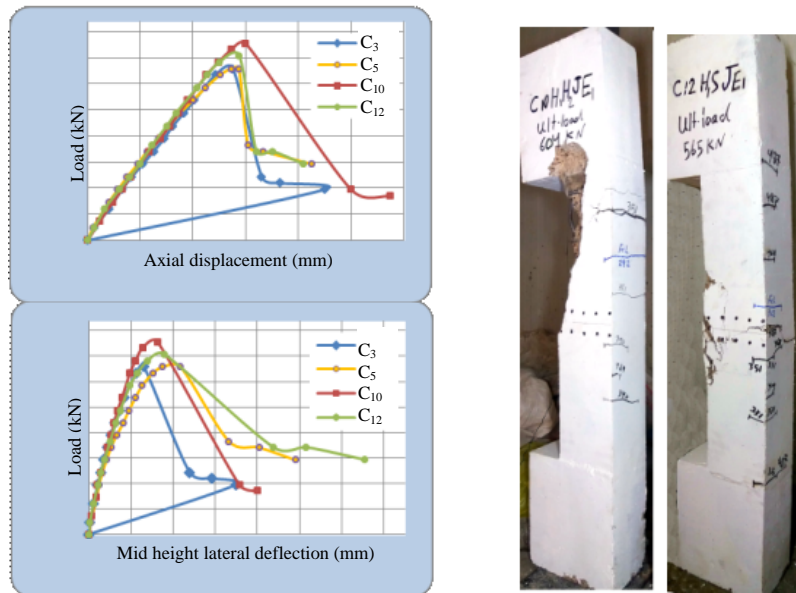


Fig. 10: a) Load-deflection of specimen C₁₀ and C₁₂ and b) Crack pattern of C₁₀ and C₁₂

507 kN), respectively. Compared with reference specimens (C₁₀ and C₁₁) there is a decrease in the cracking load about (87.18 and 14.70%), respectively, also, there is an increase in the ultimate load capacity about (23.10 and 44.44%) and the ductility was increased (5.78-11.65%), respectively. Figure 12a and 13a show the load deflection response of

the column specimens C₁₄ and C₁₅, respectively. Figure 12b and 13b shows the crack pattern of the specimens C₁₄ and C₁₅, respectively.

Specimens C₁₆-H₁-S-J-E and C₁₇-H₂-S-J-E : These specimen are the same of the specimens C₁₂ and C₁₃ with

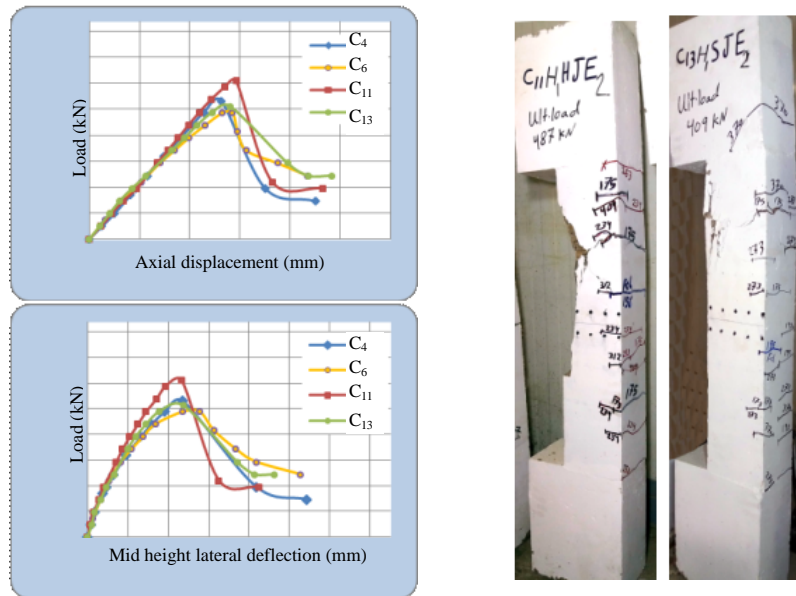


Fig. 11: a) Load-deflection of specimen C_{11} and C_{13} and b) Crack pattern of C_{11} and C_{13}

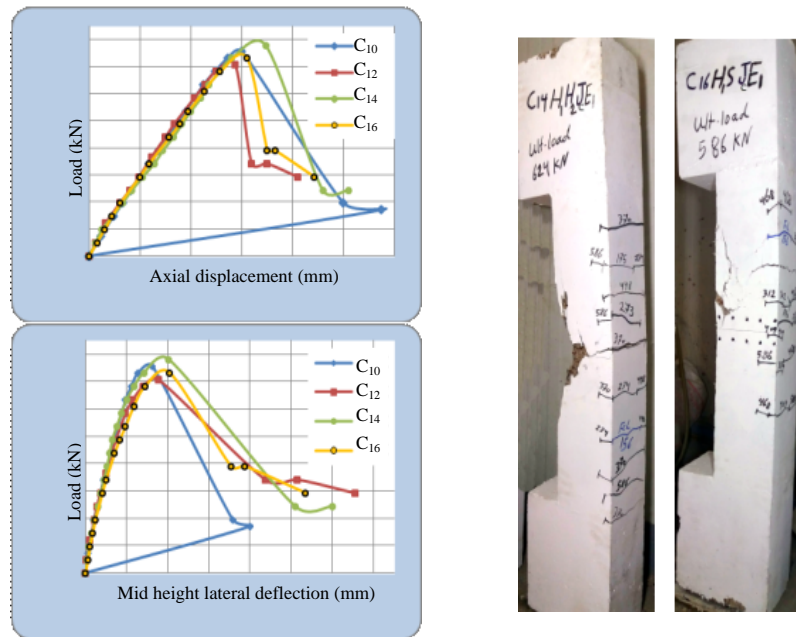


Fig. 12: a) Load-deflection of specimen C_{14} and C_{16} and b) Crack pattern of C_{14} and C_{16}

presence of shear connectors across the construction joint. The first crack in columns appeared at load (156 and 117 kN), respectively. The spalling happened on the compression side gradually at load (586 and 429 kN), respectively. Compared with reference specimens (C_{12} and C_{13}) there is a decrease in the cracking load about (100 and 66.66%), respectively,

also, there is an increase in the ultimate load capacity about (3.71 and 4.89%) and the ductility was increased (1.66, 3.89%), respectively. Figure 12a and 13a show the load deflection response of the column specimens C_{16} and C_{17} , respectively. Figure 12b and 13b show the crack pattern of the specimens C_{16} and C_{17} , respectively.

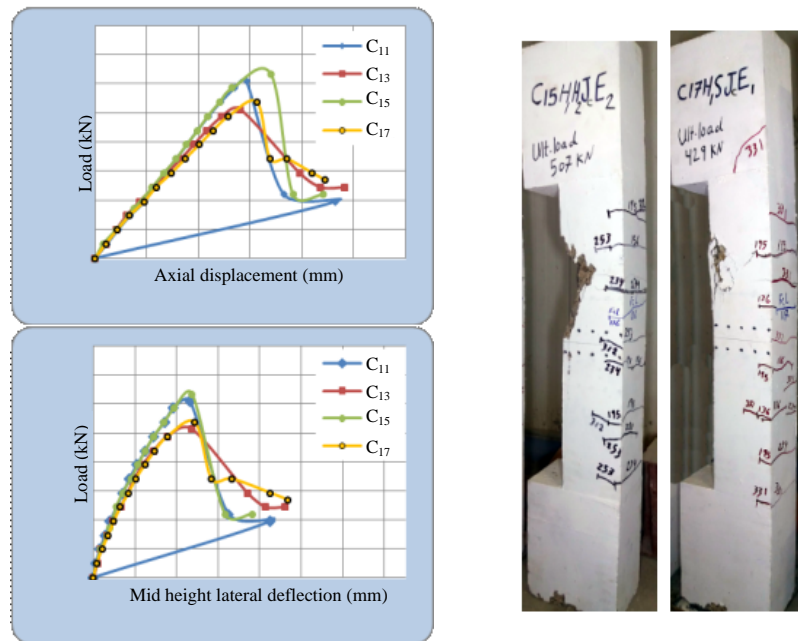


Fig. 13: a) Load-deflection of specimen C_{15} and C_{17} and b) Crack pattern of C_{15} and C_{17}

CONCLUSION

For the column specimens hybridized with concrete type H_2 in the outer shell when the (e/h) values $[(1/3)$ and $(1/2)]$, the ultimate strength was increased (3.74 and 21.08%). On the other hand, the cracking load was increased (43.38 and 16.32%), respectively.

When the (e/h) values $[(1/3)$ and $(1/2)]$, the presence of SFRC in the outer shell was improved in the load carrying capacity about (3.74 and 11.11%) and there was an enhancement the cracking loads about (100 and 50%), respectively.

For the column specimens hybridized with 50% of CFRP bars as longitudinal reinforcement when the (e/h) values $[(1/3)$ and $(1/2)]$, the ultimate strength was decreased about (3.75 and 0%). On the other hand, the cracking load was decreased (40 and 49.57%), respectively.

When the (e/h) values $[(1/3)$ and $(1/2)]$ and comparing with the column specimens with monolithic casting, the presence of construction joint between the concrete of the core and the shell led to increase in the ultimate load about (14.82 and 14.59%) and (7.41 and 4.87%) for column specimens hybridized with concrete type H_2 and SFRC in the outer shell, respectively on the other hand, the cracking load was increased about (49.74 and 14.70%) and (14.28 and 11.42%) for column specimens hybridized with concrete type H_2 and SFRC in the outer shell, respectively.

When the (e/h) values $[(1/3)$ and $(1/2)]$ and comparing with the column specimens without shear connectors, using of shear connectors in the construction joints led to increase in the ultimate load about (3.31 and 4.10%) and (3.71 and 4.89%) for column specimens hybridized with concrete type H_2 and SFRC in the outer shell, respectively on the other hand, the cracking load was decreased about (87.18 and 14.70%) and (100 and 66.66%) for column specimens hybridized with concrete type H_2 and SFRC in the outer shell, respectively.

For all the column specimens, the ductility ratio were calculated when the (e/h) values $[(1/3)$ and $(1/2)]$, the ductility ratio was decreased about (1.13 and 5.68%) for column specimens hybridized with concrete type H_2 in the outer shell but the ductility ratio was increased about (8.74 and 4.54%) for column specimens hybridized with concrete type SFRC in the outer shell, respectively using of CFRP bars (50% hybridization) was increased the ductility ratio about (1.04 and 5.43%), respectively the presence of the construction joint was decreased the ductility about (1.14, 1.80%) for column specimens hybridized with concrete type H_2 in the outer shell and about (6.25 and 2.17%) for column specimens hybridized with concrete type SFRC in the outer shell, respectively and comparing with the column specimens with monolithic casting, Also, the presence of the shear connectors was increased the ductility about (5.78 and 11.65%) for column specimens hybridized with concrete type H_2 in the outer shell and (1.66 and 3.89%) for column

specimens hybridized with concrete type SFRC in the outer shell, respectively and comparing with the column specimens without shear connectors.

REFERENCES

- Al-Haddad, W.H.M., 2016. Experimental and Theoretical Investigation for Behavior of Hybrid Reinforced Concrete Corbel-Column Connection. University of Babylon, Hillah, Iraq.
- Al-Yassiri, L.S.H., 2017. Behavior of voided reinforced concrete slabs with carbon fiber reinforced polymer bars. Ph.D Thesis, University of Babylon, Hillah, Iraq.
- Anonymous, 1983. BS 1881 116; Testing concrete: Method for determination of compressive strength of concrete cubes. BSI Group, London, England, UK. <https://www.scribd.com/document/292768848/BS-1881-116-1983-Testing-Concrete-Method-for-Determination-of-Compressive-Strength-of-Concrete-Cubes>.
- Anonymous, 2014. Building code requirements for structural concrete (ACI 318M-14) and commentary. American Concrete Institute, Michigan, USA.
- Aziz, A.H., 2006. Flexural and shear behavior of hybrid I-beams with high-strength concrete and steel fibers. Ph.D Thesis, Al-Mustansiriya University, Baghdad, Iraq.
- Mahdi, A.M., 2015. Experimental and theoretical analysis for behavior of concrete corbels with hybrid reinforcement. Msc Thesis, University of Babylon, Hillah, Iraq.
- Malik, M.M., 2015. Flexural and shear behavior of reinforced concrete T-section beams composed of hybrid concrete. MSc Thesis, University of Babylon, Hillah, Iraq.
- Richart, F.E. and R.L. Brown, 1934. An investigation of reinforced concrete columns: A report of an investigation. Msc Thesis, University of Illinois at Urbana-Champaign, Champaign County, Illinois.