

Luminescence and Lifetime of $\text{CaO-Al}_2\text{O}_3\text{-B}_2\text{O}_3\text{: Yb}^{3+}$ and $\text{CaO-Al}_2\text{O}_3\text{-B}_2\text{O}_3\text{: Ce}^{3+}$ Rare-Earth-Doped Borate Glasses

^{1,3}G.R. Barrera, ^{1,2}A.L.F. Novais, ¹A.S. Almeida, ¹L.F. Souza, ¹C.M. Abreu,
³F.T. Galindo, ²F.C.L. Ferreira and ¹N. Souza

¹Departament of Física, Universidade Federal de Sergipe,
Av. Marechal Rondon, s/n 49100-00 Sao Cristovao, SE, Brasil

²Universidade Federal do Sul e Sudeste do Para-UNIFESSPA,

Folha 31, Quadra 07, Lote Especial., s/n 68507-590, Nova Maraba-Maraba, PA, Brasil

³Corporacion Universitaria del Huila-CORHUILA,

Call 21 No. 6-01/Prado Alto: Calle 8 No. 32-49 Huila, Colombia

Abstract: This recherche aimed to investigate the characteristics related to the photo luminescence properties of borate glasses $\text{CaO-Al}_2\text{O}_3\text{-B}_2\text{O}_3$ doped with 1.0% of Yb^{3+} and Ce^{3+} . These glasses were prepared by using a melt-quenching technique and characterized through X-Ray Diffraction (XRD) and Fourier-transform infrared spectroscopy and photo luminescence and decay spectral studies to determine the feasibility of using these glasses as luminescent devices in the visible region. The XRD standard confirmed the amorphous nature of the prepared glasses. By means of the infrared spectra the vibrational characteristics of the borate glass groups were verified. The characterization showed that the levels of rare-earth ions did not compromise the structural properties of the glassy matrixes. Excitation and luminescence spectra and fluorescence lifetime of the rare-earths ions were also detected. The excitation and emission spectra of both glasses show a broad PL profile due to the $^2\text{F}_{5/2} \rightarrow$ and $5d \rightarrow 4f$ transitions for Yb and Ce dopant, respectively.

Key words: Excitation, luminescence, spectra and fluorescence, life time of the rare-earths, ions, characterization

INTRODUCTION

Glasses doped with Rare-Earth Ions (REIs) have attracted great attention in the scientific community because of their capability to control properties such as refractive index, density, structure, luminescence and optical absorption by variation of oxide admixtures and composition (Barbi *et al.*, 2018; Mahamuda, 2013). The simplicity of synthesis of these glassy materials, the durability of their thermal, mechanical and chemical properties, the ability to manufacture optical elements of any shape and size, their relatively low cost, the possibility to incorporate impurities and their high optical homogeneity makes them ideal for application in devices such as photo chromic sun screen lenses, phosphor lamps, active laser hosts, scintillators and dosimeters (Jafari *et al.*, 2014; Sontakke *et al.*, 2016; Tripathi *et al.*, 2016).

Borate glasses are one of the most promising oxide glasses for applications in optical devices because of their spectroscopic and structural characteristics (Parandamaiah *et al.*, 2015; Swapna *et al.*, 2014; Luo *et al.*, 2016; Barrera *et al.*, 2019). These

glasses have high linear refractive indices and marked optical non linearities when compared to other vitreous materials (Kassab *et al.*, 2002; Mallur *et al.*, 2015).

The optical properties of REIs in glasses depend on the chemical composition of the glass matrix, its structure and the nature of the chemical bonds (Kadono, 2007; Mahamuda *et al.*, 2013). Ce^{3+} -doped inorganic materials such as glasses and crystals are widely used as phosphors for displays and lighting as well as high-energy radiation scintillations (Wisniewski *et al.*, 2008; Bachmann *et al.*, 2009; Ueda *et al.*, 2011). This is due to the superior light yield of Ce^{3+} ions arising from their parity-allowed $5d\text{-}4f$ transitions (Sontakke *et al.*, 2016). The absence of cross-relaxation mechanisms and an insignificant multiphonon relaxation of the excitation population, due to the wide gap between $5d$ and $4f$ energy level have established Ce^{3+} as one of the most efficient luminescent ions (Barbi *et al.*, 2018). Yb^{3+} glass is a promising material with numerous attractive properties (Biswal *et al.*, 1999) including good spectroscopic and laser performance parameters with a broad fluorescence spectrum (compared to and amplify ultrashort laser pulses (Kassab *et al.*, 2002).

Addition of Al₂O₃ to the oxide glass structure affects different physical properties such as glass transition temperature (T_g), density and refractive index (Yue *et al.*, 2018). The structural role of Al₂O₃ in oxide glasses is important because this oxide has insufficient oxygen to form a tetrahedral network. Al³⁺ ions become 4-coordinated with oxygen if there are enough oxygen ions from October 18, 2019 the modifier oxides in the glass (El-Moneim *et al.*, 2003). Also, the simultaneous filling up of the vacancies (empty spaces) amidst the borate network present by the interstitial Ca²⁺ metal ions increases the compactness of the glass and consequently the measured density. Therefore an appropriate addition of CaO to the glass contributes to a dense glass body (Luo *et al.*, 2016; El-Moneim *et al.*, 2003).

Rare-earth-doped glasses have shown a good sensitivity for absorbing UV-visible radiation and emitting visible radiation that may make them promising candidates for sensing electromagnetic radiation. Due to this in the current study, Calcium Aluminoborate (CaO-Al₂O₃-B₂O₃) matrix glass was used as host for REIs in both Yb³⁺- and Ce³⁺-doped glasses. To this purpose, we scrutinize the optical excitation, luminescence decay kinetics and the structural and amorphous nature of these borate glasses.

MATERIALS AND METHODS

The proposed glass compositions were prepared using the conventional melt-quenching technique. Raw materials and rare-earth dopants used were: CaO, Al₂O₃, H₃BO₃, Yb₂O₃ and Ce₂O₃ (SigmaAldrich, 99.99% purity). The proposed composition ratios used to prepare the glass samples were: 27% CaO-18% Al₂O₃-55% B₂O₃:1.0 wt.% of Yb³⁺ (CAB:Yb³⁺) and 27% CaO-18% Al₂O₃-55% B₂O₃:1.0 wt.% of Ce³⁺ (CAB:Ce³⁺). The above mentioned materials were weighed and the powders well mixed for 30 min in an agate mortar before being melted in a porcelain crucible in an electric furnace at 1100°C for 60 min with a heating rate of approximately 20°C/min.

The molten mixtures were stirred frequently to ensure homogeneity and then poured into a pre-heated aluminum mold at 200°C. The amorphous structures were confirmed by X-Ray Diffraction (XRD) in a Rigaku DMAX 2000 CuKα diffractometer with the tube operating at 40 kV/20 mA with steps 2θ(°) = 0.5 in the 2θ scan range of 10° < 2θ < 80° with 10 sec per step at room temperature. For these analyses, grain sizes of <75 nm were used.

The local structure of lead borate glass and lead aluminum borate were studied by Fourier Transform Infrared (FTIR) spectroscopy. The spectra were obtained in the range of 4000-400 cm⁻¹ at room temperature in a varian 640 spectrometer (typical resolution of 4 cm⁻¹ and 64 accumulations). The samples were in the form of KBr pellets (discs). The excitation and emission spectra were obtained using a spectrofluorometer (Nanolog-Horiba) with an R928P photo multiplier tube equipped with

a xenon lamp (CW 450 W) as excitation source and a 399 nm filter. Lifetime was also obtained with the nano log using the same lamp and the same detector.

RESULTS AND DISCUSSION

XRD spectral analysis: The glasses are amorphous materials with absence of crystalline periodicity. The XRD patterns of the two glass samples are shown in Fig. 1. The spectra show the absence of any sharp peak and the presence of broad humps which confirms the amorphous nature of the rare-earth-doped borate glasses. This behavior indicates that the samples are not crystalline and corroborate with the formation of vitreous structures. The XRD patterns of both materials are very similar but with a difference in intensity located between 20 and 40° for CAB: Yb³⁺ sample. The presence of dopant is only factor to caused this difference in intensity, since, the same synthesis procedure for both samples, this will also be discussed in section 3.3.

FTIR spectral analysis: Information related to the arrangement of structural groups of the studied glasses was explained with the help of FTIR spectroscopy. The FTIR spectra of the glasses CAB:Ce³⁺ and CAB: Yb³⁺ are shown in Fig. 2. The broad composite bands extending to

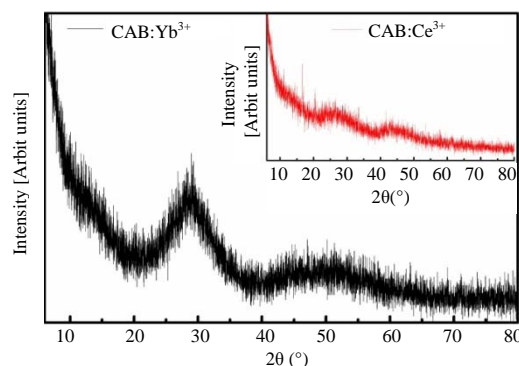


Fig. 1: XRD pattern of glass CAB: Yb³⁺

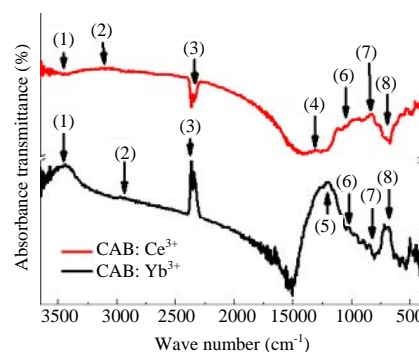


Fig. 2: FTIR spectra of CAB:Yb³⁺ and CAB:Ce³⁺ glasses. The peaks were identified according to Table 1

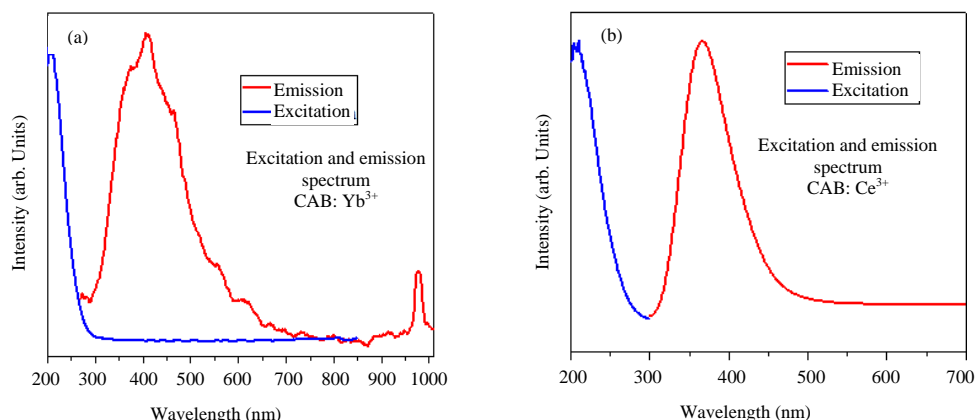


Fig. 3(a, b): (a) Photo luminescence excitation and emission spectra for CAB: Yb³⁺ samples using excitation at 250 nm and emission at 410 and 976 nm and (b) Photoluminescence excitation and emission spectra for CAB: Ce³⁺ samples with excitation at 280 nm and emission at 367 nm

the near-infrared region $\sim 3415\text{ cm}^{-1}$ (CAB: Ce³⁺) and $\sim 3419\text{ cm}^{-1}$ (CAB: Yb³⁺) are due to hydroxyl, water or B-OH groups present in the samples. The presence of these hydroxyl or water groups could be attributed to the experimental procedure (KBr technique) and may also arise due to the presence of water in H₃BO₃ (Balachander *et al.*, 2013). The spectra show peaks at $\sim 2927\text{ cm}^{-1}$ (CAB: Ce³⁺) and $\sim 2923\text{ cm}^{-1}$ (CAB: Yb³⁺) which are attributed to the presence of hydrogen bonding in the glass sample (Sharma *et al.*, 2006; Balachander *et al.*, 2013). Finally, the borate glasses in the study show three active infrared spectral regions. The region at 600-800 cm⁻¹ is attributed to the bending vibrations of borate segments. The other, at 850-1200 cm⁻¹ is attributed to the stretching vibration of structural groups containing BO₄ tetrahedra such as diborate, triborate, tetraborate and pentaborate groups (Aronne *et al.*, 1999; Galeener *et al.*, 1980). Peaks at $\sim 828\text{ cm}^{-1}$ (CAB: Ce³⁺) and $\sim 826\text{ cm}^{-1}$ (CAB: Yb³⁺) are due to the BO₄⁻ stretch (tri, tetra and pentaborates). The bands centered at $\sim 1024\text{ cm}^{-1}$ (CAB: Ce³⁺) and $\sim 1021\text{ cm}^{-1}$ (CAB: Yb³⁺) in these studied systems confirm the presence of asymmetric stretching of tetrahedral BO₄ units and vibrations of diborates bridging to pentaborate (Balachander *et al.*, 2013). The region between 1200 and 1500 cm⁻¹ arises from the B-O stretching vibration of BO₃ units such as metaborate chains and rings and pyroborate and orthoborate groups (Kamitsos *et al.*, 1990). The broad peak centered at $\sim 1326\text{ cm}^{-1}$ present in the CAB: Ce³⁺ glass spectrum is associated with B(3)-O-B(4) stretching vibrations in the glass net stretching (Saddeek *et al.*, 2010). The shoulder at $\sim 1236\text{ cm}^{-1}$ exhibited by the glass CAB: Yb³⁺ can be attributed to asymmetric stretching vibrations of B-O bond in metaborate's pyroborates and orthoborates (Gautam *et al.*, 2012). It is important to note

that BO₄ structural units can be formed with the incorporation of CaO and Al₂O₃ in the network of the studied glasses (Saddeek *et al.*, 2010).

Each oxide of CaO or Al₂O₃ can convert two BO₃ units into two BO₄ units (Saddeek *et al.*, 2010). These spectra exhibit broad absorption bands because of the general disorder in the network, due mainly to the wide distribution of structural units occurring in these glasses. The FTIR spectral peaks are detailed in Table 1.

Photoluminescence spectral analysis: The photo luminescence excitation spectrum for a 1 wt.% Yb³⁺ doped CAB glass, corresponding to the ²F_{5/2}-²F_{7/2} transition is presented in Fig. 3a. The peaks related to Yb³⁺ was observed at 976 nm and is assigned to transitions from the first level of the excited to the ground state. The most intense emission band has a peak at about 410 nm extending across the visible range. This emission band can be attributed to the formation of Yb³⁺ clusters in the glass structure-such a characteristic of clusters formation resulting in visible emission due to energy transfer from ytterbium as a dopant has been confirmed in the literature (Schaudel *et al.*, 2000, Oppo *et al.*, 2012). The band of emission cooperative present in the sample of the work published by Schaudel *et al.*, 2000, resemble the spectrum obtained for the CAB: Yb³⁺ glasses.

The interesting fact here is that the excitation spectrum does not exhibit a band in the visible region (Fig. 2a). As an ultraviolet excitation (250 nm) was used to obtain the emission peak in the infrared region, the excitation of the cluster and the isolated ions of ytterbium is attributed to the occurrence of energy transfers from the vitreous matrix to the clusters and ions, since, the electronic transitions of Yb corresponding to the ²F_{5/2}-²F_{7/2} transition are excited in the infrared (Biswal *et al.*, 1999).

Table 1: Peak table of FTIR spectra of CAB: Ce³⁺ and CAB: Yb³⁺ glasses

Order	CAB: Ce ³⁺ (cm ⁻¹)	CAB: Yb ³⁺ (cm ⁻¹)	Assignment	Researcher
1	~3415	~3419	Hydroxyl or water or B–OH groups	Balachander <i>et al.</i> (2013)
2	~2927	~2923	Hydrogen bonding	Sharma <i>et al.</i> (2006)
3	~2342	~2342	Presence of atmospheric CO ₂	Schadle <i>et al.</i> (2016)
4	~1326	~1236	B(3)–O–B(4), B–O stretching	Saddeek <i>et al.</i> (2010) Gautam <i>et al.</i> (2012)
5	~1024	~1021	BO ₄ group stretching	Pal <i>et al.</i> (2011)
6	~828	~826	BO ⁺ stretching (tri, tetra pentaborates)	Aronne <i>et al.</i> (1999) Galeener <i>et al.</i> (1980)
7	~696	~695	BO ₄ vibrations	Aronne <i>et al.</i> (1999) Galeener <i>et al.</i> (1980)

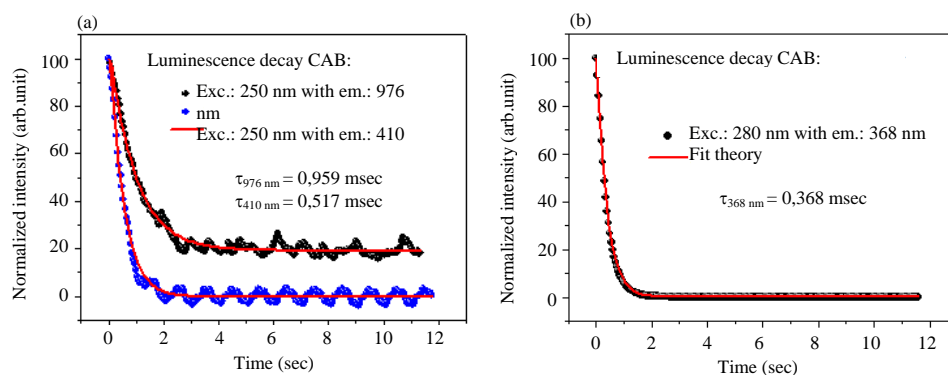


Fig. 4(a, b): The luminescence decay curves for CAB:Yb³⁺ and CAB:Ce³⁺

The ytterbium ions cluster formation and vitreous matrix components can be confirmed by the luminescent decay times shown in Fig. 4a. A decay time of $\tau = 0.959$ ms was observed for the emission at 976 nm and another one of $\tau = 0.517$ ms for the emission at 410 nm. These results corroborate with the decay times observed by Schaudel *et al.* (2000) in the study on the luminescent properties of ytterbium doped inborosilicate glass. Figure 3b shows PL emission and excitation spectra of CAB: Ce³⁺ sample. The Ce-doped samples exhibit an emission band between 320-460 nm, centered at 367 nm under excitation wave length of 280 nm. This emission is assigned to the 5d-4f transitions from the first excited state to the ground state. Such wavelength emission agreed well with reported value for other Ce doped glasses (Nakauchi *et al.* 2017). The luminescent decay time observed for the emission at 367 nm was 0.517 msec as shown in Fig. 4b.

Although, the emission and excitation spectra of CAB: Ce³⁺ agree with the one obtained by Nakauchi *et al.* (2017) when studied other aluminoborate glass doped with Ce, the order of magnitude of luminescent decay time of CAB: Ce³⁺ glass is three times greater. Emission Ce³⁺ centers have usually fast decay time from 50-60 nsec, approximately (Nakauchi *et al.* 2017). However, the luminescent decay time can be change by the interaction between doping ion and other ions present in the structure by non-irradiative energy transfer (Kucera *et al.* 2013). As spectroscopic properties depend on the lattice and

composition of the glass, then this result confirm that cerium ion was added as a dopant to the CAB glass structure.

CONCLUSION

New Calcium Aluminoborate glasses, CAB: Yb³⁺ and CAB: Ce³⁺ were synthesized and studied using different spectroscopic techniques. The XRD spectra confirmed the amorphous nature of the as-prepared glasses. From the XRD spectra of the glasses investigated, a difference in intensity was observed between 20 and 40°; this difference was related due to the dopant. It was found from the FTIR spectra that different structural borate groups are present in these glasses. By means of the FTIR spectra it was observed that BO₄ structural units can be formed with the incorporation of CaO and Al₂O₃ in the network of the glasses studied.

Each CaO or Al₂O₃ oxide can convert two BO₃ units into two BO₄ units. The excitation and emission spectra of both glasses show a broad PL profile due to the and 5d-4f transitions for Yb and Ce dopant, respectively. An emission band centered at about 410 nm extending across the visible region was observed to CAB: Yb³⁺ and attributed by the formation of Yb³⁺ clusters. These features enable the use of these new material as candidates for the development of devices that operate in the near visible and infrared spectral regions.

ACKNOWLEDGEMENTS

We would like to acknowledge the support received from the Brazilian agencies CAPES and CNPq and from the Corporacion Universitaria del Huila-CORHUILA.

REFERENCES

- Aronne, A., S. Esposito and P. Pernice, 1999. FTIR and DTA study of structural transformations and crystallisation in BaO-B₂O₃-TiO₂ glasses. *Phys. Chem. Glasses*, 40: 63-68.
- Bachmann, V., C. Ronda and A. Meijerink, 2009. Temperature quenching of yellow Ce³⁺ luminescence in YAG: Ce. *Chem. Mater.*, 21: 2077-2084.
- Balachander, L., G. Ramadevudu, M. Shareefuddin, R. Sayanna and Y.C. Venudhar, 2013. IR analysis of borate glasses containing three alkali oxides. *Sci. Asia*, 39: 278-283.
- Barbi, S., C. Mugoni, M. Montorsi, M. Affatigato, C. Gatto and C. Siligardi, 2018. Structural and optical properties of Cerium Oxide doped barium bismuth borate glasses. *J. Non-Cryst. Solids*, 499: 183-188.
- Barrera, G.R., L.F. Souza, A.L.F. Novais, L.V.E. Caldas and C.M. Abreu *et al.*, 2019. Thermoluminescence and optically stimulated luminescence of PbO-H₃BO₃ and PbO-H₃BO₃-Al₂O₃ glasses. *Radiat. Phys. Chem.*, 155: 150-157.
- Biswal, S., J. Nees, A. Nishimura, H. Takuma and G. Mourou, 1999. Ytterbium-doped glass regenerative chirped-pulse amplifier. *Opt. Commun.*, 160: 92-97.
- El-Moneim, A.A., A.M. AbdEl-Daiem and I.M. Youssof, 2003. Ultrasonic and structural studies on TiO₂-doped CaO-Al₂O₃-B₂O₃ glasses. *Phys. Status Solidi*, 199: 192-201.
- Galeener, F.L., G. Lucovsky and J.C. Mikkelsen Jr, 1980. Vibrational spectra and the structure of pure vitreous B₂O₃. *Phys. Rev. B*, 22: 3983-3990.
- Gautam, C., A.K. Yadav and A.K. Singh, 2012. A review on infrared spectroscopy of borate glasses with effects of different additives. *ISRN. Ceram.*, Vol. 2012, 10.5402/2012/428497
- Jafari, S.M., D.A. Bradley, C.A. Gouldstone, P.H.G. Sharpe and A. Alalawi *et al.*, 2014. Low-cost commercial glass beads as dosimeters in radiotherapy. *Radiat. Phys. Chem.*, 97: 95-101.
- Kadono, K., 2007. Nonoxide glass-forming systems-glass formation and structure and optical properties of rare-earth ions in glasses. *J. Ceram. Soc. Jpn.*, 115: 297-303.
- Kamitsos, E.I., A.P. Patsis, M.A. Karakassides and G.D. Chryssikos, 1990. Infrared reflectance spectra of lithium borate glasses. *J. Non-Cryst. Solids*, 126: 52-67.
- Kassab, L.R.P., L.C. Courrol, N.U. Wetter, L. Gomes, V.L.R. Salvador and A.S. Morais, 2002. Lead fluoroborate glass doped with ytterbium. *J. Alloys Compd.*, 344: 264-267.
- Kucera, M., M. Nikl, M. Hanus and Z. Onderisinova, 2013. Gd³⁺ to Ce³⁺ energy transfer in multi-component GdLuAG and GdYAG garnet scintillators. *Phys. Status Solidi (RRL) Rapid Res. Lett.*, 7: 571-574.
- Luo, X., L. Ren, W. Xie, L. Qian, Y. Wang, Q. Sun and H. Zhou, 2016. Microstructure, sintering and properties of CaO-Al₂O₃-B₂O₃-SiO₂ glass/Al₂O₃ composites with different CaO contents. *J. Mater. Sci. Mater. Electron.*, 27: 5446-5451.
- Mahamuda, S.K., K. Swapna, A.S. Rao, M. Jayasimhadri, T. Sasikala, K. Pavani and L.R. Moorthy, 2013. Spectroscopic properties and luminescence behavior of Nd³⁺ doped Zinc Alumino bismuth borate glasses. *J. Phys. Chem. Solids*, 74: 1308-1315.
- Mallur, S.B., T. Czarnecki, A. Adhikari and P.K. Babu, 2015. Compositional dependence of optical band gap and refractive index in lead and bismuth borate glasses. *Mater. Res. Bull.*, 68: 27-34.
- Nakauchi, D., G. Okada, Y. Fujimoto, N. Kawano, N. Kawaguchi and T. Yanagida, 2017. Optical and radiation-induced luminescence properties of Ce-doped magnesium aluminoborate glasses. *Opt. Mater.*, 72: 190-194.
- Oppo, C.I., R. Corpino, P.C. Ricci, M.C. Paul and S. Das *et al.*, 2012. Incorporation of Yb³⁺ ions in multicomponent phase-separated fibre glass preforms. *Opt. Mater.*, 34: 660-664.
- Pal, M., B. Roy and M. Pal, 2011. Structural characterization of borate glasses containing Zinc and Manganese Oxides. *J. Mod. Phys.*, 2: 1062-1066.
- Parandamaiah, M., K.N. Kumar and S.V. Reddy, 2015. Spectroscopic properties of Eu 3-doped Lithium Sodium bismuth borate glasses for red luminescent optical devices. *Int. J. Eng. Sci.*, 5: 16-22.
- Saddeek, Y.B., M.S. Gaafar and S.A. Bashier, 2010. Structural influence of PbO by means of FTIR and acoustics on calcium alumino-borosilicate glass system. *J. Non-Crystalline Solids*, 356: 1089-1095.
- Schadle, T., B. Pejčić and B. Mizaikoff, 2016. Monitoring dissolved Carbon dioxide and Methane in brine environments at high pressure using IR-ATR spectroscopy. *Anal. Methods*, 8: 756-762.
- Schaudel, B., P. Goldner, M. Prassas and F. Auzel, 2000. Cooperative luminescence as a probe of clustering in Yb³⁺ doped glasses. *J. Alloys Compd.*, 300: 443-449.
- Sharma, G., K. Singh, S. Mohan, H. Singh and S. Bindra, 2006. Effects of gamma irradiation on optical and structural properties of PbO-Bi₂O₃-B₂O₃ glasses. *Radiat. Phys. Chem.*, 75: 959-966.

- Sontakke, A.D., J. Ueda and S. Tanabe, 2016. Effect of synthesis conditions on Ce^{3+} luminescence in borate glasses. *J. Non-Cryst. Solids*, 431: 150-153.
- Swapna, K., S. Mahamuda, A.S. Rao, S. Shakya, T. Sasikala, D. Haranath and G.V. Prakash, 2014. Optical studies of Sm^{3+} ions doped zinc alumino bismuth borate glasses. *Spectrochim. Acta Part A. Mol. Biomol. Spectrosc.*, 125: 53-60.
- Tripathi, H., A.S. Kumar and S.P. Singh, 2016. Preparation and characterization of $Li_2O-CaO-Al_2O_3-P_2O_5-SiO_2$ glasses as bioactive material. *Bull. Mater. Sci.*, 39: 365-376.
- Ueda, J., S. Tanabe and T. Nakanishi, 2011. Analysis of Ce^{3+} luminescence quenching in solid solutions between $Y_3Al_5O_{12}$ and $Y_3Ga_5O_{12}$ by temperature dependence of photoconductivity measurement. *J. Applied Phys.*, 110: 53102-53126.
- Wisniewski, D., L.A. Boatner, J.O. Ramey, M. Wisniewska, J.S. Neal and G.E. Jellison, 2008. Exploratory research on the development of novel Ce^{3+} -activated Phosphate glass scintillators. *IEEE. Trans. Nucl. Sci.*, 55: 3692-3702.
- Yue, Y., Y. Wang, Y. Cao, S. Chen, Q. Zhou, W. Chen and L. Hu, 2018. Effect of Al_2O_3 on structure and properties of $Al_2O_3-K_2OP_2O_5$ glasses. *Opt. Mater. Express*, 8: 245-258.