



Journal of Applied Sciences

ISSN 1812-5654

science
alert

ANSI*net*
an open access publisher
<http://ansinet.com>

Utilization of Carbamoyethylated Cotton for Heavy Metal Ion Removal

¹Kh.M. Mostafa and ²Hassan Al-Bar

¹National Institute for Standard, El-Haram, P.O. Box 136 Giza, Egypt

²Department of Chemistry, Faculty of Science, King Abdul Aziz University, Jeddaha (21589)

Abstract: Cotton cellulose in fabric form was rendered ion exchanger via Carbamoyethylation Reaction (CER). The latter was carried out using acrylamide (Aam) and sodium hydroxide. The resulted carbamoyethylated cotton having amide functional groups (CONH₂) was monitored for its ability to adsorb heavy metals from their aqueous solutions. Different factors affecting adsorption of metal ions onto the latter substrate such as metal ion concentration, pH, treatment time and temperature were studied systematically. Results obtained reflect the following findings: (a) the adsorption value increases by increasing the metal ion concentration up to 60 m mol L⁻¹ then levels off, (b) the carbamoyethylated cotton was found to be selective adsorbent for Hg²⁺ at pH 0.5, (c) the adsorption values is higher at 40°C then levels off by raising the temperature to 60 and 80°C, respectively, (d). The adsorption values increase by increasing the treatment time up to 5 h at 40 and 60°C and 3 h at 80°C then levels off and (e) The adsorption values of the aforementioned substrate in question at different metal ions follow the order: Hg²⁺ > Cu²⁺ > Zn²⁺ > Co²⁺ > Pb²⁺.

Key words: Carbamoyethylated Cotton (CEC), adsorption value, metal ions

INTRODUCTION

Environmental pollution caused by toxic heavy metals in industrial effluents is considered as one of the most important problems worldwide^[1]. The use of synthetic resins for chelating toxic metal ions in wastewater is considered as a possible way for preventing environmental pollution. These resins are mostly based on petroleum synthetic polymers^[2-5] at which secondary environmental pollution take place via their contamination on soil and air. In addition, these synthetic polymers are usually none renewable and non-biodegradable.

So, present research has been directed to use chemically modified cotton as an agriculture biopolymer, low cost as well as renew ability for heavy metal ion removals, instead of original cotton due to it has no chelating or interaction capacity. Hence, several trials have been made to utilize cotton cellulose as a metal scavenger, by using modified cotton containing glycidyl methacrylate, diethyl aminoethyl methacrylate and acrylic acid^[6], DEAE-cotton-g-poly (MAA)^[7], phosphorylated cotton^[8], DEAE, carbamoyl ethyl and poly (Aam)^[9], acrylic acid/N-methylol acrylamide mixture^[10], cellulose/glycidyl methacrylate/acrylic acid cation exchange composites^[11]. This study has been undertaken with the aim to removal of some heavy metals via chelation on the aforementioned carbamoyethylated cotton having the amide groups. The different factors affecting adsorption of metal ions such

as metal ion concentration, pH, treatment time and temperature as well as durability were studied in detail.

MATERIALS AND METHODS

Cotton fabric (400 g m⁻², 21 Picks x 61 ends/cm) kindly supplied by Misr Spinning and Weaving Co., El-Mehalla El-Kubra. It was used after purification by scouring for 2 h at the boil using aqueous solution containing 1% sodium hydroxide. It was then thoroughly washed and air-dried at room temperature. Acrylamide, sodium hydroxide, hydrochloric acid, cyclohexane, mercuric chloride, copper sulphate, zinc acetate, nickel chloride and lead acetate were reagent grade chemicals.

Preparation of Carbamoyethylated cotton having 605 mmol amide group/100 g sample (capacity): The freshly prepared catalyst NaOH (1 mL) of concentration 0.25 N and 4 mL cyclohexane was added to complete the total volume to 10 mL. The reaction mixture was shaken very well and allowed to proceed at 40°C for 1 h in a thermostatic water bath.

Metal salts: Hg (NO₃)₂, Cu (COOCH₃)₂.H₂O, Zn (COOCH₃)₂, Co(COOCH₃)₂.4H₂O and Pb (COOCH₃)₂.3H₂O were of analytical reagent grade.

Adsorption of metal ions: Aqueous solutions of 0.01 M of different metal salts were prepared and its pH was

adjusted to the specified values. The cotton (0.5 g) was put into a glass bottle containing 50 mL of the metal salts solution and the mixture was occasionally shaken for the desired treatment time. The adsorption value was calculated by estimating the metal ion concentration before and after treatment with carbamoylethylated cotton by titration against standard EDTA.

Desorption of metal ions: The treated carbamoylethylated cotton with metal ions was stirred with 50 mL of 0.1 N nitric acid for 2 h at room temperature and then filtered. Then the metal ion in the filtrate was estimated.

RESULTS AND DISCUSSION

Effect of metal ion concentration: Figure 1 shows the adsorption values (expressed as m mol/100 g sample) of different metal ions concentration on carbamoylethylated cotton. It is shown in the Fig. 1 that:

- The adsorbed amounts of metal ions increase by increasing metal ions concentration from 20-60 m mol/100 g sample then levels off.
- The maximum adsorption value was 430 m mol /100 g sample for Hg^{2+} and the minimum was 173 m mol/100 g sample for Pb^{2+} .
- The adsorption values depend on the metal ion used and follow the order: $\text{Hg}^{2+} > \text{Cu}^{2+} > \text{Zn}^{2+} > \text{Co}^{2+} > \text{Pb}^{2+}$.

This is in accordance with Irving-William's series^[12] for the stability of various ligands with nitrogen or oxygen as coordinating atoms for divalent metal ions.

Effect of pH: Figure 2 represents the adsorption values (expressed as m mol/100 g sample) of different metal ions at different pH values (0.5 - 6.0) of carbamoylethylated cotton. The results obtained reflect the following findings:

- The adsorption values of metal ions in question increases by increasing the pH values within the range studied.
- At pH value 0.5 only Hg^{2+} metal ion adsorbed and the adsorption value was 220 m mol/100 g samples. This reflects the role of amide group in carbamoylethylated cotton as selective adsorbent for Hg^{2+} at pH 0.5.
- At pH value 1 the adsorbed metal ions were Hg^{2+} and Cu^{2+} and the adsorption values were 260 and 40 m mol/100 g samples, respectively.
- At pH range 2.0-6.0 all metal ions used were adsorbed with different values depending on the nature of metal ion and the substrate used.
- The adsorption values depend on the metal ion used and follow the order: $\text{Hg}^{2+} > \text{Cu}^{2+} > \text{Zn}^{2+} > \text{Co}^{2+} > \text{Pb}^{2+}$.

Effect of treatment time and temperature: Table 1 clarifies the adsorption of metal ions at different duration (0.5-24 h) and temperatures (40-80°C) of carbamoylethylated cotton.

The adsorption of metal ions increases by increasing treatment time within the range studied to reach a maximum value the levels off. The maximum adsorption values occur after 5 h at 40 and 60°C and 3 h at 80°C, respectively.

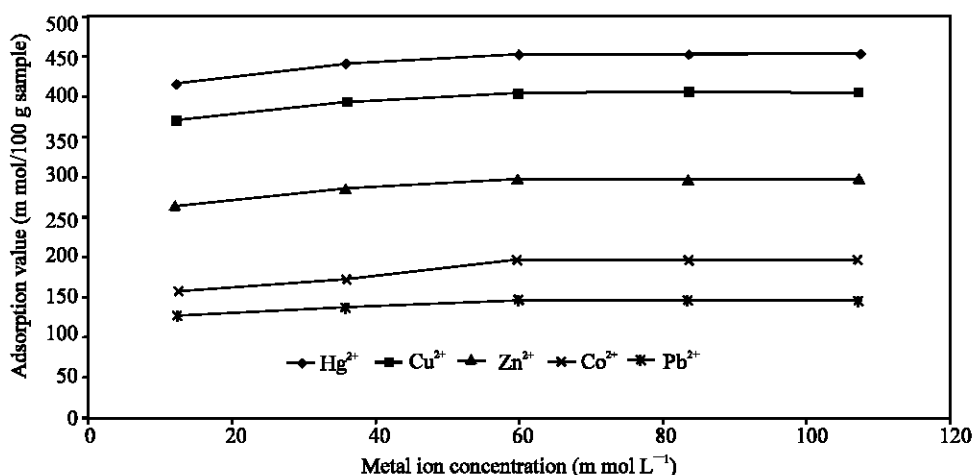


Fig. 1: Effect of metal ion concentration on the adsorption value (expressed as m mol/100 g sample) of different metal ions of carbamoylethylated cotton
Reaction conditions: Carbamoylethylated Cotton, 0.5 g; total volume of metal ion, 50 mL; pH, 6.0, treatment time, 24 h and temperature, 40°C.

Table 1: Effect of changing treatment time and temperature on the adsorption value (m.mol/100 g sample) of different metal ions of carbamated cotton

Metal ion	Adsorption value (m mol/100 g sample)														
	40°C					60°C					80°C				
	½ h	1 h	3 h	5 h	24 h	½ h	1 h	3 h	5 h	24 h	½ h	1 h	3 h	5 h	24 h
Hg ²⁺	270	325	380	430	430	245	290	350	385	385	210	245	280	280	280
Cu ²⁺	260	300	355	390	390	230	265	310	350	350	195	215	250	250	250
Zn ²⁺	235	260	280	300	300	205	225	240	265	265	185	210	225	225	225
Co ²⁺	160	180	205	215	215	150	165	180	200	200	135	185	205	205	205
Pb ²⁺	130	145	165	173	173	110	135	155	165	165	100	115	140	140	140

Reaction conditions: Carbamoylethylated cotton, 0.5 g; metal ion concentration, 60 m mol L⁻¹ Total volume of metal ion, 50 mL; pH, 6.0.

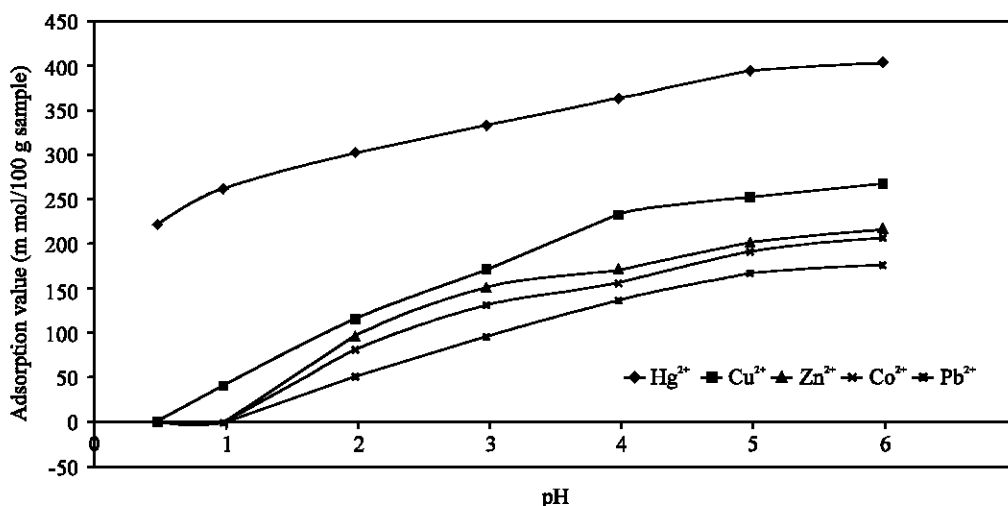


Fig. 2: Effect of pH on the adsorption value (expressed as m mol/100 g sample) of different metal ions of carbamoylethylated cotton

Reaction conditions: Carbamoylethylated Cotton, 0.5 g; metal ion concentration, 60 mmol L⁻¹; total volume of metal ion, 50 mL; pH, 6.0, treatment time, 24 h and temperature, 40°C.

Table 2: The adsorption of different metal ions on the Carbamoylethylated Cotton (adsorption and desorption)

Metal ion	Adsorption value (m mol/100 g sample) after;			
	0 Cycle	5 Cycles	10 Cycles	20 Cycles
Hg ²⁺	430	430	430	430
Cu ²⁺	390	390	390	390
Zn ²⁺	300	300	300	300
Co ²⁺	215	215	215	215
Pb ²⁺	173	173	173	173

The adsorption values of metal ions decreases by raising the treatment temperature from 40 to 60°C and then to 80°C. This can be explained in terms of the higher stability of the chelate formed at lower temperatures as generally observed for low molecular weight complexes. This observation is in agreement with that obtained with Nakamora *et al.*^[13].

Durability: Carbamoylethylated cotton was used in adsorption and desorption of different metal ions several times (20 cycles) to examine its durability. Table 2 shows that adsorbed metal ions were easily desorbed by

treatment with 0.1 M HNO₃ at room temperature. The adsorbed amount of the different metal ions remains unchanged after 5, 10, 15 and 20 cycles, which reflect the excellent durability of the above mentioned substrate (Table 2).

CONCLUSIONS

It was found that, higher adsorption value of different metal ion obtained at: metal ion concentration, 60 m mol L⁻¹ pH, 6.0, treatment time, 5 h; treatment temperature, 40°C when using the metal ion solution 50 mL.

ACKNOWLEDGEMENTS

I wish to express my deepest thank and appreciation to the spirit of Prof. Dr. M.I. Khalil Prof of Textile Chemistry, National Research Center for his valuable discussion, great support as well as all the facilities provided for terminating this work.

REFERENCES

1. Shany, S.K. and J. Reedijk, 1984. Coordination chemistry of chelating resins and ion exchangers. *Coordination Chemistry Reviews*, 59: 1.
2. Egawas, H., T. Nonaka, S. Abe and M. Nakayama, 1992. Recovery of uranium from seawater. *J. Applied Polymer Sci.*, 45: 837.
3. Lee, T.S. and S.I. Hong, 1995. Porous chelating resins from poly (acrylonitrile-co-ethylacrylate-co-divinylbenzene). *Pure and Applied Chem.*, A, 32: 379.
4. Lezzi, A. and S. Cobianco, 1994. Chelating resins supporting dithiochromate and methylthiourea groups in adsorption of heavy metal ions. *J. Applied Polymer Sci.*, 45: 889.
5. Liu, C.Y., M.J. Chen, N.M. Lee, H.C. Hawang, S.T. Jou and J.C. Hsu, 1992. Synthesis and coordination behaviour of hydroxamate with varying spacer group. *Polyhedron*, 11: 551.
6. Hebeish, A., A. Waly, F.A. Abdel-Mohdy and A.S. Aly, 1997. Synthesis and characterization of cellulose ion exchanger. 1. Polymerization of glycidyl methacrylate, dimethylaminoethyl methacrylate and acrylic acid with cotton cellulose using thiocarbonate- H_2O_2 redox system. *J. Applied Polymer Sci.*, 66: 1029-1037.
7. Hebeish, A. and Z.H. El-Hilw, 1998. Preparation of DEAE cotton-g-poly (methacrylic acid) for use as ion exchanger. *J. Applied Polymer Sci.*, 6: 739-745.
8. Nada, A., M. Abd-Allah and L.M. Hassan, 2003. Phosphorylated cation-exchanger from cotton stalks and their constituents. *J. Applied Polymer Sci.*, 89: 2950-2956.
9. El-Hilw, Z.H., 1999. Synthesis of cotton-bearing DEAE, carbamoyl ethyl, carboxyethyl and poly (acrylamide) graft for utilization in dye removal. *J. Applied Polymer Sci.*, 73: 1007-1014.
10. Ibrahim, N.A. and M.H. Abo-Shosha, 1993. Novel cation-exchange composites resulting from polymerization/cross-linking of acrylic acid/N-metholacrylamide mixtures with cellulose. *J. Applied Polymer Sci.*, 49: 291-298.
11. Ibrahim, N.A. and M.H. Abo-Shosha, 1995. Preparation and characterization of cellulose/glycidyl methacrylate/acrylic acid cation exchange composites. *Acta Polymerica*, 46: 50-55.
12. Irving, H. and R.J.P. Williams, 1956. Coordination chemistry review. *Nature*, 162: 746 (1948); *Chem. Rev.*, 56: 271.
13. Nakamura, S., M. Amano, Y. Saegusa and T. Sato, 1992. Chelating stability of low molecular weight complexes. *J. Applied Polymer Sci.*, 45: 265.